Designer carbon nanotubes for contaminant removal in water and wastewater: A critical review

Binoy Sarkar [a,b#], Sanchita Mandal [a], Yiu Fai Tsang [c], Pawan Kumar [d], Ki-Hyun Kim [e,*], Yong Sik OK [f,g*]

[a] *Future Industries Institute, University of South Australia, Mawson Lakes, SA 5095, Australia*

[b] *Department of Geological Sciences, Indiana University, Bloomington, IN 47405, USA*

[c] *Department of Science and Environmental Studies, The Education University of Hong Kong, Tai Po, New Territories, Hong Kong*

[d] *Department of Nano Science and Materials, Central University of Jammu, Jammu 181143, India*

[e] *Department of Civil and Environmental Engineering, Hanyang University, Seoul 04763, Korea*

[f] *Korea Biochar Research Center, Kangwon National University, Chuncheon 24341, Republic of Korea*

[g] *O-Jeong Eco-Resilience Institute (OJERI) & Division of Environmental Science and Ecological Engineering, Korea University, Seoul, Republic of Korea*

[#] Current address: Department of Animal and Plant Sciences, The University of Sheffield, Western Bank, Sheffield, S10 2TN, UK


[*]Corresponding authors:

soilok@kangwon.ac.kr; kkim61@hanyang.ac.kr

Highlights

- CNTs can be designed through specific functionalization or modification process.
- Designer CNTs can enhance contaminant removal efficiency.
- CNTs can facilitate recovery and regeneration of nanomaterials.
- CNTs hold potential applications in wastewater purification and desalination.
- Further research is needed to enhance commercial acceptance of CNTs.

Graphical abstract

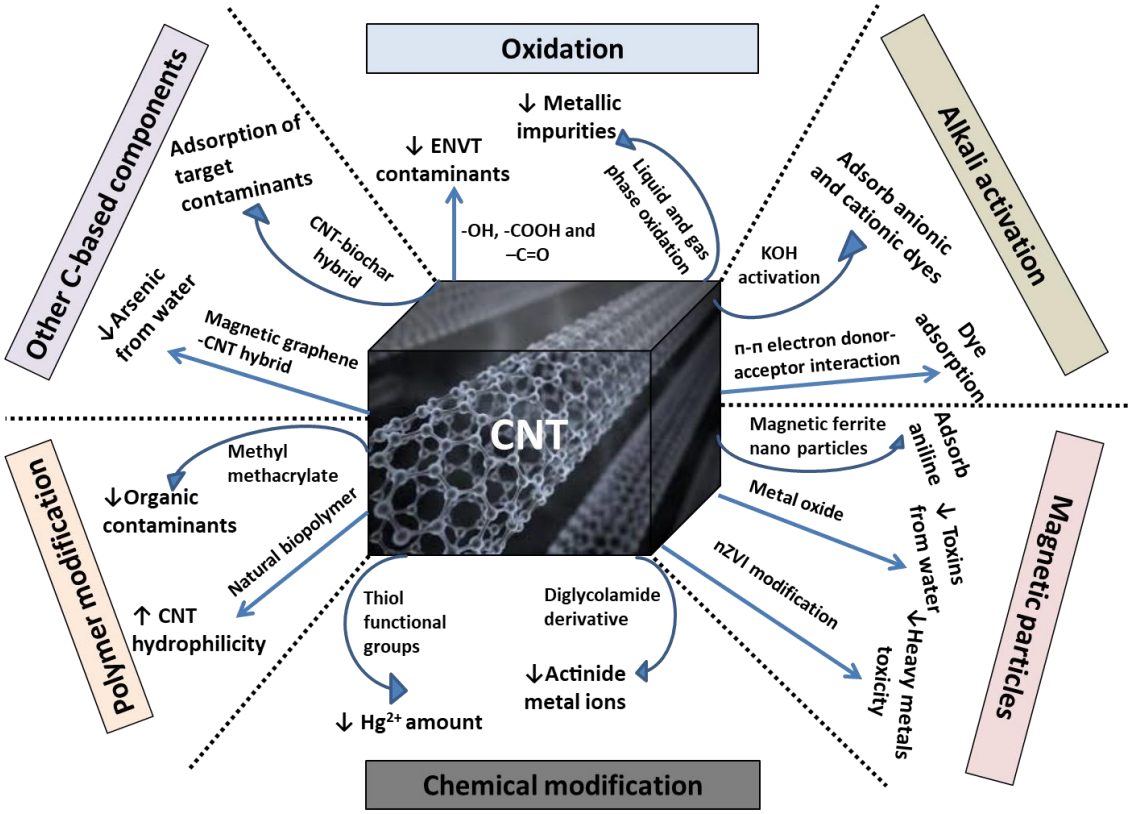

Contents

1. Introduction
2. CNT structure and types
3. CNTs for various environmental applications
    3.1 Adsorbents
    3.2 Membranes
    3.3 Catalysts
    3.4 Sensors
    3.5 Oil spill sponges
4. Functionalization/modification of CNTs for environmental application
    4.1 Oxidation
    4.2 Alkali activation
    4.3 Modification with magnetic particles
    4.4 Modification with nonmagnetic metal oxide
    4.5 Modification with zero-valent iron
    4.6 Specific chemical derivatization or modification
    4.7 Modification with polymer
    4.8 CNT immobilization
    4.9 Modification with other carbon based adsorbents
5. Contaminant treatment by CNTs
    5.1 Emerging contaminants
    5.2 Heavy metals, metalloids and radionuclides
    5.3 Organic dyes
    5.4 Pesticides
6. CNT-based water treatment technologies

6.1 Drinking water purification

6.2 Desalination

7. Interactions of CNTs with environmental colloids

8. Economic assessment

9. Conclusions and future research directions

ABSTRACT

The search for effective materials for environmental cleanup is a scientific and technological issue of paramount importance. Among various materials, carbon nanotubes (CNTs) possess unique physicochemical, electrical, and mechanical properties that make them suitable for potential applications as environmental adsorbents, sensors, membranes, and catalysts. Depending on the intended application and the chemical nature of the target contaminants, CNTs can be designed through specific functionalization or modification processes. Designer CNTs can remarkably enhance contaminant removal efficiency and facilitate nanomaterial recovery and regeneration. An increasing number of CNT-based materials have been used to treat diverse organic, inorganic, and biological contaminants. These success stories demonstrate their strong potential in practical applications, including wastewater purification and desalination. However, CNT-based technologies have not been broadly accepted for commercial use due to their prohibitive cost and the complex interactions of CNTs with other abiotic and biotic environmental components. This paper presents a critical review of the existing literature on the interaction of various contaminants with CNTs in water and soil environments. The preparation methods of various designer CNTs (surface functionalized and/or modified) and the functional relationships between their physicochemical characteristics and environmental uses are discussed. This review will also help to identify the research gaps that must be addressed for enhancing the commercial acceptance of CNTs in the environmental remediation industry.

Keywords: Carbon nanotubes; Surface functionalization/modification; Contaminants; Environmental remediation; Soil remediation; Desalination

1. Introduction

The earth is continuously being contaminated with numerous toxic substances from both natural and anthropogenic sources. Rapid population growth and increasing industrial development have caused the discharge of various toxic elements, compounds, and/or materials into the environment. Many new chemicals have been introduced for use without proper assessment of their environmental risks and human health impacts. The discharge of untreated industrial effluent into water and soil, the indiscriminate use of pesticides and fertilizers in agriculture, the unregulated use of harmful chemicals in consumer products, the lack of proper public sanitation systems in developing countries, the combustion of fossil fuels, the weathering of toxic elements from rocks and minerals, and the over-extraction of ground water are some of the primary causes of contamination of water, soil, and air. This environmental issue is worsening day by day as modern society faces ever increasing cases of deaths due to diseases, such as cancer. Although industrial and agricultural growth and the use of new chemicals are necessary to maintain human civilization, the scientific community has a huge responsibility to develop effective technologies for cleaning up the environment.

The search for effective and low-cost materials that can eliminate present and future harmful contaminants and treat hazardous wastes in the environment is a scientific and technological issue of paramount importance. Scientists around the world have been searching for various materials - either of natural or synthetic origin - to fit into the purpose of environmental remediation. However, conventional materials (e.g., zeolite, clay minerals, and agricultural/ industrial waste-based adsorbents) often experience drawbacks in practical applications, including (i) poor contaminant removal capacity, (ii) lack of contaminant interaction specificity, and (iii) environmental instability (Sud et al., 2008; Bhatnagar and Sillanpää, 2010; Bhatnagar et al., 2011; Sarkar et al., 2012; Perego et al., 2013). Some adsorbents prepared from industrial and municipal waste materials may also pose risks of secondary pollution (Bhatnagar

and Sillanpää, 2010). In this context, carbon materials, such as activated carbon and biochar, occupy a unique position in the hierarchy of adsorbent materials for eliminating toxic substances in air, water, and soil (Mohan et al., 2014; Ok et al., 2015). Activated carbon and biochar may also encounter a number of problems when applied under the field conditions, such as poor adsorption specificity and biofouling. In addition, over the last decade, carbon nanotubes (CNTs) and graphene-based materials have seen an extensive use for environmental remediation (Mauter and Elimelech, 2008; Apul and Karanfil, 2015; Perreault et al., 2015).

In recent decades, CNTs have attracted the attention of scholars worldwide. These nanomaterials possess distinctive mechanical, electrical, thermal, and other properties that qualify them for applications in electronics, light sources, lightweight but high-strength polymer composites, sensors, nanoprobes in high-resolution imaging, nanoelectrodes, and hydrogen reservoirs (Baughman et al., 2002; De Volder et al., 2013).

This tiny crystalline form of active carbon also holds enormous potential in the field of environmental remediation, which has so far been less explored compared with other methods (Upadhyayula et al., 2009; Ren et al., 2011; Schnorr and Swager, 2011; Ersan et al., 2016). CNTs are emerging as one of the most promising remediation materials because of their large specific surface area, high porosity, light weight, and desirable interactions with a diverse range of contaminants (Ren et al., 2011; Gupta et al., 2013; Yu et al., 2014; Apul and Karanfil, 2015; Patiño et al., 2015). CNTs could outperform activated carbon in terms of practical applications in water treatment because of the nanoparticles' excellent self-assembling ability on supporting materials via chemical vapor deposition (Karwa et al., 2006), as well as their immobilization ability in membranes and filters (Hylton et al., 2008; Mishra and Ramaprabhu, 2010). On the other hand, CNTs may impose some unwanted impacts on environmental receptors (Cañas et al., 2008; Boncel et al., 2015; Chen et al., 2015; Vithanage et al., 2017).

140 The current paper presents a critical review of existing literature on the interactions of
141 various contaminants with CNTs in water and soil environments. Some recent reviews focused
142 on CNT-based adsorption against specific types of contaminants in aqueous solutions (Gupta
143 et al., 2013; Yu et al., 2014; Apul and Karanfil, 2015; Patiño et al., 2015; Lee et al., 2016;
144 Santhosh et al., 2016). However, information regarding the functional relationship between
145 CNT modification/functionalization and environmental application of the designer products is
146 still limited. Therefore, this review aims to highlight the preparation methods of various
147 designer CNTs (surface functionalized and/or modified) and to assess the relationships between
148 their physicochemical characteristics and environmental uses in a holistic approach.
149

150 **2. CNT structure and types**

151 CNTs are composed of enrolled cylindrical graphitic sheets (known as graphene sheets) in
152 which carbon atoms are arranged in sp^2 hybridization at the corners of hexagons (Thostenson
153 et al., 2001) (Fig. 1). The seamless cylinders give rise to an outer diameter from about 1 to
154 30 nm (Aqel et al., 2012). CNTs have nanometer-sized diameters but micrometer-sized lengths,
155 which should yield a length-to-diameter ratio greater than 1,000 (Popov, 2004; Aqel et al.,
156 2012). Previous studies have investigated the structural properties of CHTs (e.g., diameter,
157 length, purity, defect, porosity, chirality, multi-wall vs. single-wall, straight vs. helical tubes,
158 and individual vs. bundled structure) (Iijima and Ichihashi, 1993; Ajayan, 1999; Charlier, 2002;
159 Wepasnick et al., 2010; Moradi et al., 2012). Two commercially available forms of CNTs,
160 namely single-walled carbon nanotube (SWCNT) and multi-walled carbon nanotube
161 (MWCNT), are commonly used as environmental adsorbents (Collins et al., 2000; Penza et al.,
162 2004; 2007). Rolling of a single graphene layer into a cylindrical shape gives the SWCNT,
163 while rolling of many concentric SWCNTs into a tubular shape produces the MWCNT (Iijima
164 and Ichihashi, 1993). The interlayer distance in MWCNTs is nearly 0.33 nm, which is

approximately the same as the distance between graphene layers in graphite (Aqel et al., 2012). Other CNT-related structures, which are less known for environmental applications, include nanobud (fullerene combined with CNT), graphenated CNT (graphitic foliates along the side wall of MWCNT), peapod (fullerene trapped inside CNT), torus (doughnut-shaped CNT), and cup-stacked CNT (stacked microstructure of graphene layers) (Ren et al., 2013).

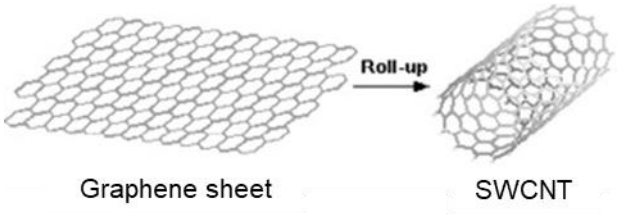


Fig. 1. Formation of CNT from graphene sheet (Aqel et al., 2012)

A number of techniques, including chemical vapor deposition (CVD), laser ablation, and arc discharge have been employed for CNT synthesis (Prasek et al., 2011). One of the most common routes of CNT synthesis is CVD through vapor deposition of the desired carbon precursor on a suitable catalyst surface (Endo et al., 2006; Prasek et al., 2011). CVD is attractive because it allows tailored control on the CNT architecture for a highly advanced field of electronics and optoelectronics while being easily scalable (Terranova et al., 2006). Transition metal nanoparticles, especially iron, cobalt, nickel, and yttrium, either alone or grafted on suitable supporting materials (e.g., silica, alumina, zeolite, and other metal oxides), are favorably selected for the nucleation and growth of CNTs (Harutyunyan et al., 2009). The role of CNTs in applications lies in the variables, such as architecture, carbon precursor, carbon feeding gas, temperature, pressure, density, and chemical environment (Terranova et al., 2006).

3. CNTs for various environmental applications

A range of physico-chemical properties of CNTs can be explored to employ the materials in environmental applications (e.g., adsorbent, membranes/filter, catalyst, oil spill sponge, and sensors) (**Fig. 2**).

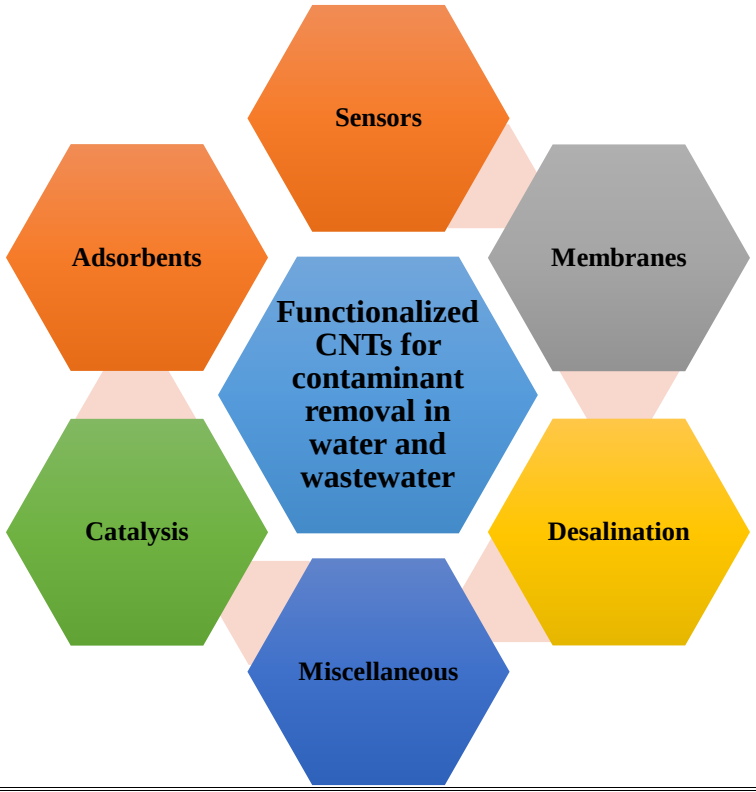


Fig. 2. Diverse classes of environmental applications of functionalized CNTs.

3.1. Adsorbents

The basic properties of CNTs (e.g., large specific surface areas and high chemical/thermal stabilities) make such materials attractive for adsorbing contaminants from water and wastewater. The adsorption properties of CNTs have been investigated against a series of toxic agents in water and wastewater, such as Pb, Cd, and 1,2-dichlorobenzene. For example, Hadavifar et al. (2014) reported the adsorption of Hg(II) from wastewater by amino- and thiol-functionalized MWCNTs. The above functional groups were introduced onto the CNT sidewalls by sequential reactions with ethylenediamine, cyanuric chloride, and sodium 2-mercaptoethanol. Adsorption isotherm and kinetic data were fitted by Langmuir and pseudo-

second-order models, respectively. The thiol-functionalized MWCNTs generally removed Hg(II) more efficiently than amino-functionalized MWCTS from wastewater (Hadavifar et al., 2014).

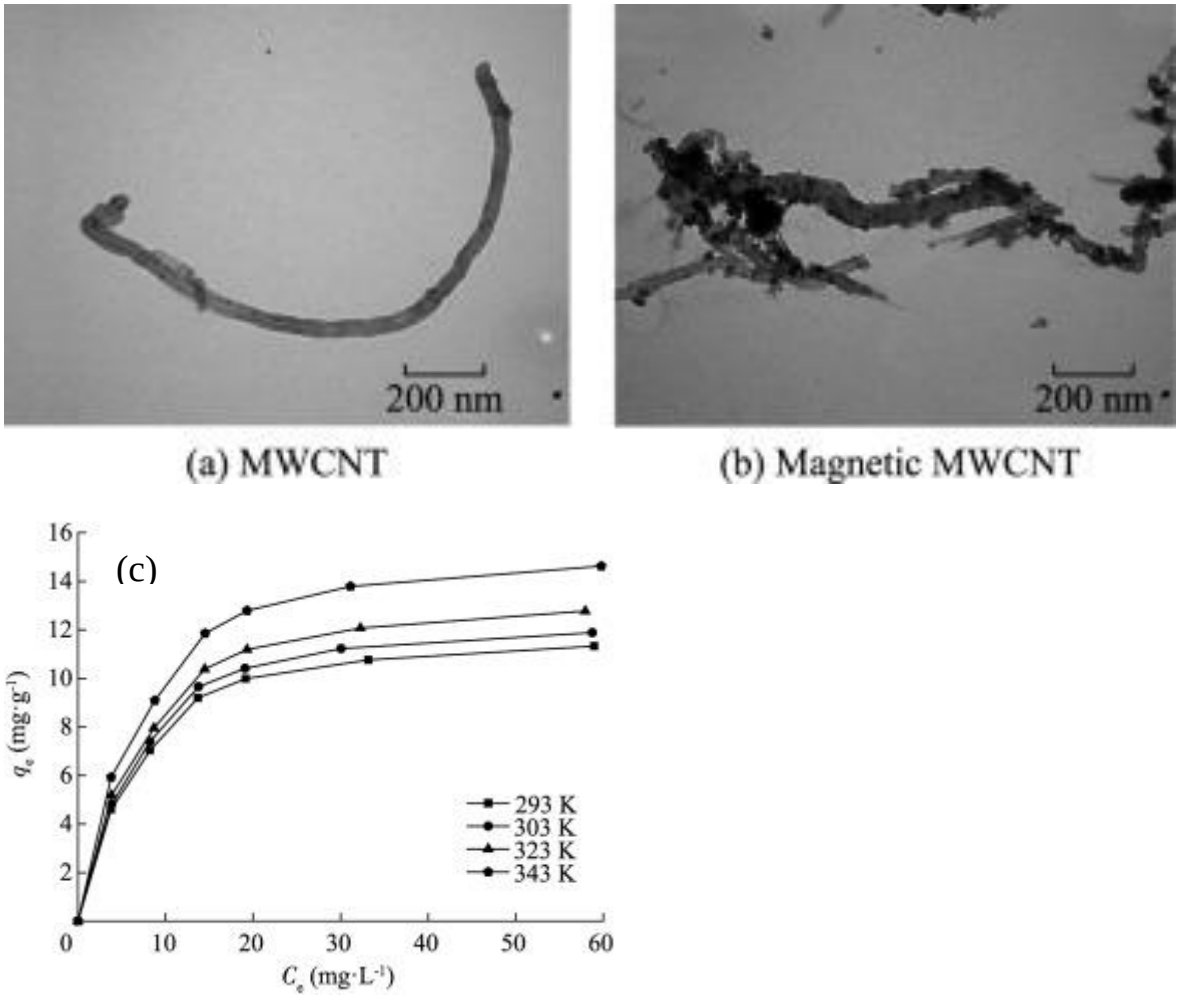


Fig. 3. (a, b) TEM images of (a) MWCNTs and (b) magnetic MWCNTs, and (c) adsorption isotherm of Cr(VI) for magnetic MWCNTs (Huang and Chen, 2014).

The removal of Cr(VI) by magnetic MWCNTs from wastewater was also investigated (Huang and Chen, 2014) (**Figs. 3 a and b).** An increase in the initial adsorbate concentration and prolonged contact time increased the Cr(VI) adsorption capacity of the magnetic MWCNTs. However, the adsorption capacity decreased with increasing adsorbent dosage. The

pseudo-second-order model best explained the kinetic behavior of the adsorption process. The calculated value of the Gibbs free energy demonstrated a thermodynamically spontaneous, and endothermic adsorption process with an enthalpy deviation of 3.835 kJ mol^{-1}. Many studies have been conducted to confirm whether CNTs are highly effective adsorbents for eliminating various harmful substances in water and wastewater (section 4).

3.2. Membranes

High stability, considerable flexibility in use and large surface area enable the development of CNT membrane filters as highly effective treatment media for chemical and biological contaminants in water and wastewater (Jame Sadia and Zhou, 2016). For example, Liu et al. (2015) investigated electrochemically active CNT filters for eliminating organic pollutants from wastewater using a point-of-use treatment technology (**Fig. 4**). Since H_2O_2 alone could not remove phenolic species effectively from the system, H_2O_2 was activated anodically to generate radical species. With an average oxidation rate of 0.059 ± 0.001 mol h^{-1} m^{-2}, the removal efficiency of phenol was stable at 87.0 ± 1.8% continuously over 4 h. Such removal was influenced by the combined effects of several variables (e.g., electrode material, cathode potential, pH, flow rate, and dissolved oxygen) (Liu et al., 2015). This work demonstrated the potential of developing inexpensive filtration technology using CNTs to meet the ever-increasing demand of adequate clean water.

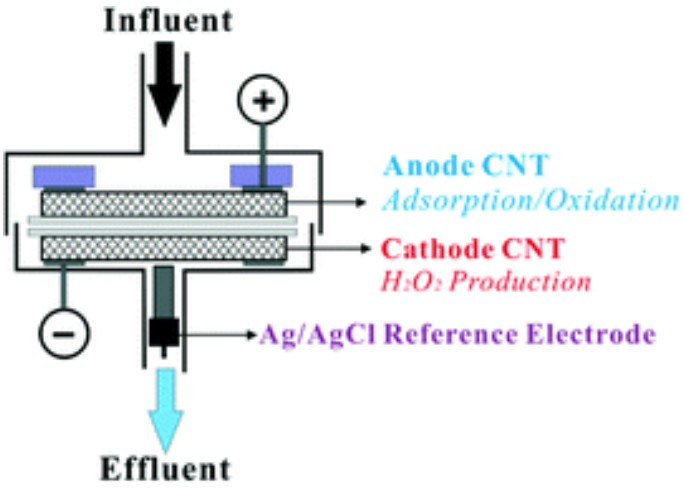


Fig. 4. Schematic of CNT-filter based electrochemical wastewater treatment system having *in situ* H_2O_2 generation assembly (Liu et al., 2015).

3.3. Catalysts

Among all options, the use of CNTs as a catalyst is also promising, especially for wastewater treatment. This potential is due to their mesoporous nature, exceptional mechanical strength, graphitic structure enabled support of specific metals, large surface area, and electrical/chemical/thermal characteristics. For example, Garcia et al. (2006) used different ruthenium (Ru) precursors and impregnation methods to prepare ruthenium/MWCNT catalysts. The MWCNT surface was subsequently treated with high strength aniline in wastewater using wet air oxidation. The Ru/MWCNT-COOH catalyst synthesized from 1,5-cyclooctadiene and 1,3,5-cyclooctatriene precursors yielded 100% conversion of aniline in about 45 min reaction time (Garcia et al., 2006). Stability of the catalyst was found to be directly linked with Ru loading and the strength of Ru-CNT interaction (Garcia et al., 2006). Recently, Jamie et al. (2016) reported the immobilization of a lipase enzyme (extracted from *Candidia rugose*) on modified MWCNTs and application of the CNT-biocatalyst for oily wastewater treatment. Surface oxidation level of MWCNTs, type of cross-linkers and their concentrations dominantly controlled the loading and subsequent catalytic activity of the

MWCNT-supported enzyme. The CNT-immobilized enzyme yielded approximately 93 times higher catalytic activity than the free enzyme (Jamie et al., 2016).

3.4. Sensors

Desirable properties of CNTs, including non-metallic nature, electronic transport, minute size per amount of material, and thermopower (voltages between junctions caused by interjunction temperature differences) can be exploited for environmental sensing applications (Jijun et al., 2002; Chakrapani et al., 2003; Penza et al., 2004; Kazachkin et al., 2008). As such, their applications have been validated from diverse fields or modes, including resistive sensors, capacitive sensors, chemical field effect transistors, gas ionization sensors, thermoelectric response, and CNT-aided optical (or acoustic) sensors. For example, Karimi-Maleh et al. (2014) prepared a highly sensitive electrochemical sensor using a ZnO/CNT nanocomposite to detect hydrazine in wastewater in the presence of phenol. The authors achieved simultaneous detection of hydrazine and phenol in wastewater at as low as 8.0 nmol L^{-1} concentrations using square wave voltammetry (SWV) technique (3σ) (Karimi-Maleh et al., 2014).

A selective Hg(II) sensor was developed by adsorbing cold mercury vapor on SWCNTs in industrial wastewater (Safavi et al., 2010). Various levels of Hg(II) adsorption on SWCNTs yielded differential impedances in the adsorbent material, and monitoring of these impedance values allowed to sense as low as 0.64 μg mL^{-1} Hg(II) in different types of wastewater samples (Safavi et al., 2010). Recently, de Oliveira et al. (2015) investigated CNTs based on voltametric sensors to detect anthraquinone hair dyes in wastewater. Glassy carbon electrodes modified with MWCNTs (activated in the presence of sulfuric acid) performed the detection of anthraquinone in water samples at ultra-low concentration (2.7×10^{-9} mol L^{-1}) (de Oliveira et al., 2015). Likewise, a carbon paste electrode was prepared by modifying ZnO-CNT composite with 8,9-dihydroxy-7-methyl-12H-benzothiazolo[2,3-b]quinazolin for detecting

hydroxylamine in water the presence of phenol and sulfite (Gupta et al., 2015). In water and wastewater samples, the nanocomposite showed 0.04, 0.1 and 0.3 µM detection limits for hydroxylamine, phenol and sulfite, respectively (Gupta et al., 2015). Overall, CNT-based sensors have exhibited good analytical performance, good sensitivity, and excellent stability for real world applications. Thus, the use of CNT-based sensors can be further extended to direct/real world applications in water and wastewater samples.

3.5. Oil spill sponges

The practical application of CNT-based materials in oil spill cleanup in sea water has been demonstrated in several studies. The management of oil spill in the sea can be more challenging than that of a land spill because oil spreads quickly over a large area with sea waves and wind. Owing to their rapid oil adsorption capacity, CNTs are considered an efficient material to control oil spills under oceanic conditions (Gui et al., 2010; Lee et al., 2011; Gui et al., 2013; Ge et al., 2016; Gupta and Tai, 2016; Kayvani Fard et al., 2016). Due to many advantageous properties (e.g., large surface area and porosity, super-hydrophobicity, high selectivity, chemical inertness, and easy recyclability), the suitability of CNTs for oil spill removal has been demonstrated successfully (Ge et al., 2016; Gupta and Tai, 2016). CNTs have thus been applied for oil spill removal as sponges (Gui et al., 2010), magnetic sponges (Ge et al., 2013; Gui et al., 2013; Nagappan and Ha, 2015), vertically aligned on solid support (e.g., steel) (Lee et al., 2011), and foam (Liu et al., 2013). The incorporation of magnetic attributes to CNTs or aligning them on solid surfaces has been proven effective in recovering spent materials by following spill cleanup. After recovering, the spent materials can be easily regenerated by heat treatment or solvent washing. However, a complete desorption of all adsorbed oil may not be possible because of the tight interaction between a portion of oils and the microporous network of CNTs.

4. Functionalization/modification of CNTs for environmental applications

Depending on the intended application and the chemical nature of the target contaminants, various functional groups can be generated or introduced on CNT surfaces (at tips and sidewalls) to effectively remove environmental contaminants. Non-polar organic contaminants show high affinity to CNTs due to the interactions of aromatic rings with the CNTs (Long and Yang, 2001). However, the CNT surfaces may require functionalization or modification to improve the affinity of CNTs towards hydrophilic ions or molecules. For example, CNTs can be functionalized through chemical oxidation by incorporating oxygen-containing functional groups (e.g., –OH, –COOH and –C=O) (Zhang et al., 2003; 2009), which is supposed to improve the material's affinity to heavy metal cations (Rao et al., 2007). A more complex modification of CNT surfaces is achievable by grafting guest molecules, which have high affinity toward a particular contaminant. For example, *β*-cyclodextrin grafted MWCNTs significantly improved the adsorption of Pb (Hu et al., 2010). Furthermore, polyaniline grafted MWCNTs demonstrated better removal of aniline and phenol (Shao et al., 2010), and alumina coated MWCNTs showed higher affinity toward heavy metal cations (Gupta et al., 2011b).

4.1. Oxidation

Surface oxidation has been the most common and easiest technique to create oxygen-containing –OH, –COOH and –C=O groups on CNT structures. Oxidation is typically performed under a refluxing condition in the presence of a single or a mixture of inorganic acids (e.g., HNO_3 and H_2SO_4) and an oxidizing agent (e.g., H_2O_2, $KMnO_4$, and NaOCl). Acid treatment is often carried out just after CNT synthesis to eliminate metallic impurities (e.g., the catalysts used for CNT synthesis) from products. After acid treatment, CNTs are either ready for direct environmental applications or have surface reaction sites that facilitate the grafting

of guest moieties on the surface to incorporate additional functionalities (Chen et al., 2009c; Cho et al., 2010; Mishra et al., 2010; Fang and Chen, 2012; Wei et al., 2017). Gas-phase oxidation of CNT surfaces was also carried out through heat treatment (Nagasawa et al., 2000) or plasma treatment (Yu et al., 2011) under O_2 gas. However, liquid-phase oxidation is more extensively used for both removing metal impurities and functionalizing products. Gas-phase oxidation may sometimes burn the thinner structure of SWCNTs (Nagasawa et al., 2000). CNT oxidation in an O_2 or CO_2 environment can etch away the tube caps causing a layer-by-layer peeling of the outer layers, which may dramatically increase the surface area of the oxidized materials (Ajayan et al., 1993; Tsang et al., 1993). Liquid- or gas-phase oxidation can also clean impure amorphous carbon from synthesized CNTs and increase the number of effective reaction sites (Datsyuk et al., 2008).

Due to their intrinsic hydrophobic behavior, CNTs do no easily disperse in polar solvents such as water, making it difficult to use this material for cleaning up contaminants from wastewater. This issue can be solved by cutting the MWCNTs to a shorter length (several hundred nm) and/or creating hydrophilic functional groups on CNT surfaces through sonication in mixed acids (Saito et al., 2002; Avilés et al., 2009). In a comprehensive study, (Datsyuk et al., 2008) found that among two acidic treatments (HNO_3 and H_2SO_4-H_2O_2 mixture), nitric acid treatment under refluxing conditions achieved the highest degree of MWCNT functionalization (e.g., nanotube shortening and generation of additional defects in the graphitic network). On the other hand, basic oxidation in NH_4OH/H_2O_2 yielded better structural integrity of MWCNTs by facilitating the maximum removal of impurities (amorphous carbon and metal oxides) (Datsyuk et al., 2008). Acid functionalization can be accelerated by microwave irradiation for 20 to 40 min (Kuo and Lin, 2009; Addo Ntim and Mitra, 2011, 2012).

353 *4.2. Alkali activation*

354 One disadvantage of CNTs relative to activated carbon is their relatively low surface area,
355 which may impose an adverse impact on contaminant adsorption. In addition, aggregation of
356 nanoparticles may result in mesoporous structure of CNTs that contains interstices and grooves
357 (Ma et al., 2012). This feature may induce strong affinitive interactions in CNTs and
358 subsequently cause structural alterations (Ma et al., 2012). Activation of carbon materials,
359 including CNTs, with alkali treatment can address this issue and effectively improve the
360 surface area and pore volume (Foo and Hameed, 2011; Ma et al., 2012). The alkali activation
361 of CNTs by Ma et al. (2012) involved heating a solid powdered mixture of MWCNTs and
362 KOH at 750 °C for 1 h under an argon atmosphere in a horizontal tube furnace. After washing
363 in concentrated HCl followed by deionized water, the dried powder successfully adsorbed dye
364 compounds (both anionic and cationic) from aqueous solutions (Ma et al., 2012). Multiple
365 interaction mechanisms, including hydrogen bonding, π–π electron-donor-acceptor interaction,
366 electrostatic interaction, and mesopore-filling, resulted in effective dye adsorption on the
367 alkali-activated MWCNTs (Ma et al., 2012). The alkali-activated CNTs were also successfully
368 used to remove toluene, ethylbenzene, and m-xylene from aqueous solutions (Yu et al., 2012).
369

370 *4.3. Modification with magnetic particles*

371 CNTs used for removing environmental contaminants from aqueous media often undergo
372 material regeneration and separation after remediation treatment. Filtration and/or high-speed
373 centrifugation may be used to separate tiny nanoparticles from a solution, however, these
374 techniques require a significant amount of energy and high cost. Thus, providing magnetic
375 properties in a designer adsorbent to develop a cost-effective technology for separating spent
376 adsorbents has gained increasing attention.

377 Simple homogeneous physical mixing of magnetic ferrite nanoparticles ($NiFe_2O_4$) prepared
378 by sol-gel method with MWCNTs using an agate mortar was reported to provide the CNTs
379 with magnetic properties (Abdel Salam et al., 2012). The composite mixture improved the
380 adsorption of aniline from the solution and subsequently eased the separation of the spent
381 adsorbent (Abdel Salam et al., 2012). However, such physical mixture of nanoparticles may
382 result in unwanted nanoparticle mobility in the environment because the individual
383 components are held together only by a weak attracting force. This operating problem can be
384 addressed by grafting the magnetic component into the composite by using suitable reaction
385 routes.

386 Incorporation of the magnetic attribute to CNTs through grafting may involve a multi-step
387 sol-gel chemical reaction, in which magnetite (Fe_3O_4) particles were first synthesized and then
388 coated with a silica layer (Guan et al., 2010). A separate sol solution of functionalized
389 MWCNTs (MWCNT-OH) was also prepared by using methyltrimethoxysilane as the sol-gel
390 precursor, poly(methylhydrosiloxane) as the deactivation reagent, and trifluoroacetic acid as
391 the stabilizing agent. The final adsorbent was prepared by mixing the above-mentioned
392 components in a conditioning environment under a nitrogen atmosphere (Guan et al., 2010). In
393 another study, magnetic iron oxide nanoparticles were incorporated on MWCNTs that were
394 covalently grafted with soluble starch (Chang et al., 2011). The resulting material improved
395 the product's hydrophilicity and enhanced its affinity toward anionic dye compounds.

396 The synthesis of magnetite (Fe_3O_4) nanoparticles on oxidized MWCNTs can be achieved
397 through a simple alkali precipitation method (Chen et al., 2009a; 2009b; Gong et al., 2009;
398 Daneshvar Tarigh and Shemirani, 2013). The synthesis protocol involved the dispersion of the
399 nanoparticles in a solution of iron and then the drop-wise addition of an alkali until the pH of
400 the mixture became >10. A slightly elevated temperature (70 – 80 °C) and reaction under an
401 inert environment were reported to provide a better yield of the oxidized iron nanoparticles.

Post-synthesis aging and/or heat treatment (~100 °C) was also beneficial. A mixed solution of ferric and ferrous forms of iron was also used to synthesize magnetite nanoparticles (Gupta et al., 2011a). Magnetic iron nanoparticle-decorated CNTs were found to remove arsenic (Mishra and Ramaprabhu, 2010), dye compounds (Qu et al., 2008), atrazine (Tang et al., 2012), and heavy metals (Wang et al., 2011) from contaminated waters.

4.4. Modification with nonmagnetic metal oxide

To achieve superior affinity toward contaminants, CNTs can be modified with various metal oxides. Transition metals, such as Fe, Zr, Ag, Ti, Ce, and bimetallic Pd-Fe (Xu et al., 2012), were successfully used for preparing metal oxide-CNT hybrids that adsorbed toxic elements (e.g., As, F, Cu, Cd, and 2,4-dichlorophenol) from water (Peng et al., 2005; Woan et al., 2009; Mishra and Ramaprabhu, 2010; Addo Ntim and Mitra, 2011; 2012; Ramamurthy et al., 2011; Venkata Ramana et al., 2013). The modification method is simple and often involves oxidative functionalization of the CNTs followed by alkali precipitation of the target metal oxide on surfaces of the nanotubes. The pre-functionalized CNTs are dispersed in the aqueous solution of the metal, and a strong alkali solution (5–7 M) is slowly added. The amount of alkali should be greater than the equivalent stoichiometric amount of the metal (final pH $\geq$ 10) to ensure that the oxidation reaction is complete. The metal oxide formation was facilitated by mild heating (85 °C) of the reaction mixture openly or under microwave irradiation (Addo Ntim and Mitra, 2011; 2012).

In most cases, the decoration of CNTs with metal oxide nanoparticles requires pre-treatment or functionalization of the CNT surfaces. However, this pre-treatment can be avoided by performing nanoparticle synthesis reaction and deposition with the aid of supercritical ethanol (An et al., 2007). A photo-reactive titania-MWCNT was successfully synthesized by the hydrolysis of titanium isopropoxide in supercritical ethanol at 270 °C for 2 h (An et al., 2007).

High-temperature annealing was not necessary to achieve the photo-reactivity; the composite was only vacuum-fired at 60 °C for 6 h. Non-magnetic Fe_2O_3 nano-catalysts were also decorated on MWCNTs by a simple impregnation of the CNTs with an aqueous $Fe(NO_3)_3$ solution followed by a 200 °C calcination for 4 h (Liao et al., 2009). The resulting catalysts were able to degrade phenolic contaminants (e.g., resorcinol and ortho-chlorophenol) in a H_2O_2-mediated Fenton reaction (Liao et al., 2009). The TiO_2-decorated MWCNTs were also used for the photocatalytic degradation of organic contaminants, such as 2,6-dinitro-p-cresol and 2,4-dinitrophenol, under solar irradiation (Wang et al., 2009a; 2009b).

4.5. Modification with zero-valent iron

Among manufactured nanoparticles, zero-valent iron (nZVI) has already received widespread attention for practical environmental remediation (Crane and Scott, 2012; Stefaniuk et al., 2016; Zou et al., 2016). Very high in-situ reactivity in the material is achieved at only a small synthesis cost, and this material is also easy to use in practical applications for contaminated groundwater remediation. Therefore, nZVI has been the most widely studied nanomaterial used for environmental remediation (Elliott and Zhang, 2001; Crane and Scott, 2012; Chekli et al., 2016). To prevent the oxidation and agglomeration of nZVI and prolong the material's reactivity, it was supported on various micro- and nano-particle supporting materials, including biochar (Mandal et al., 2017), clay minerals (Üzüm et al., 2009; Shi et al., 2011), and zeolite (Wang et al., 2010). Similarly, nZVI was also supported on CNTs and successfully used for removing hexavalent chromium (Lv et al., 2011), selenite (Sheng et al., 2016), azo dyes (Reza Sohrabi et al., 2015), and nitrobenzene (Jiao et al., 2016) from wastewater. The presence of other anions (even at high concentrations) did not affect the chromate reduction ability of designer materials (Lv et al., 2011). The decoration of MWCNTs

with nZVI can significantly enhance the contaminant removal capacity of the material (Lv et al., 2011; Reza Sohrabi et al., 2015; Jiao et al., 2016; Sheng et al., 2016).

4.6. Specific chemical derivatization or modification

Several specific chemical derivatizations or modifications of CNTs were reported to improve the material's affinity toward specific contaminant elements or compounds. Carboxyl-functionalized SWCNTs (SWCNT-COOH) were derivatized with thiol functional groups by reacting with ethanol-dissolved cysteamine hydrochloride (Bandaru et al., 2013). The reaction was conducted in the presence of N-hydroxysuccinimide and a coupling agent (e.g., 1-ethyl-(3-3-dimethylaminopropyl) carbodiimide) (Bandaru et al., 2013). Such derivatization processes may improve the dispersibility of CNTs in aqueous solutions and its affinity toward heavy metal cations, including Hg. Bandaru et al. (2013) reported that thiol-derivatized SWCNTs adsorbed a three-fold and four-fold greater amount of Hg^{2+} than unmodified SWCNTs and activated carbon, respectively. Similarly, adsorption of actinide ions was achieved by modifying MWCNTs with a ligand, such as a diglycol amide derivative (Deb et al., 2012). The biodegradation or biocompatibility of the resulting CNT adsorbent was engineered by selecting an appropriate ligand. The spent material can be easily incinerated and disposed of due to the organic component in the adsorbent. Other chemical compounds, such as β-cyclodextrin (Fuhrer et al., 2011), iodide/sulfur (Gupta et al., 2014), amino compounds (Vuković et al., 2011; Ji et al., 2012; Hamdi et al., 2015), tannic acid (Tong et al., 2011), and ethylenediamine (Vuković et al., 2010), were also used to modify CNT surfaces. The cyclodextrin molecules were also grafted on CNTs along with magnetic nanoparticles with the aid of plasma technology (Hu et al., 2010; 2011a) or polyaniline (Shao et al., 2010; 2012). Tannic acid-modified MWCNTs were reported to be excellent adsorbents of rare earth elements (e.g., La, Tb, and Lu) (Tong et al., 2011).

476

477 *4.7. Modification with polymers*

478 Various types of polymers are often used to modify CNTs and other adsorbents for
479 improving their adsorption affinity toward a particular element or compound. For example,
480 dendrimers are a unique class of polymers that successfully modify the surface of MWCNTs
481 (Eskandarian et al., 2014). The adsorbent was prepared by reacting carboxyl-functionalized
482 MWCNTs with poly(propyleneimine) dendrimer in aqueous media and the dendrimers were
483 used to adsorb single- and multi-component organic dye solutions (Eskandarian et al., 2014).

484 A plasma technique was also adopted for grafting methyl methacrylate on CNTs (Shao et
485 al., 2011). Poly(methyl methacrylate) is known to adsorb organic contaminants, however it
486 sediments rapidly in aqueous solutions, which may compromise its adsorption capacity. This
487 issue was tackled by grafting poly(methyl methacrylate) molecules on CNT surfaces, thereby
488 preventing the sedimentation of the active ingredient. Thus, the designer material successfully
489 removed 4,4′-dichlorinated biphenyl from the aqueous solutions (Shao et al., 2011).

490 Natural biopolymers can also be used to enhance the hydrophilic nature and improve
491 biocompatibility of CNTs in environmental applications. For example, Yan et al. (2012b)
492 reported the covalent grafting of guar gum onto MWCNT surfaces. During an attempt to
493 incorporate magnetic Fe_3O_4 nanoparticles into the designer material, it was found that the
494 biopolymer facilitated a better dispersion of the Fe_3O_4 nanoparticles on the adsorbent surfaces
495 through a supramolecular interaction between its hydroxyl groups and the metal ions; this
496 significantly improved the adsorption of aqueous dye contaminants (Yan et al., 2012b).

497

498 *4.8. CNT immobilization*

499 CNTs are highly resistant to degradation and may impart toxicity to environmental
500 organisms. Therefore, they should be removed from treated water. The limitation of the

techniques used to separate these small particles from water may obstruct their widespread use as adsorbents in environmental remediation. This can somehow be tackled by immobilizing CNTs in polymer-carrying electrospun fibrous membranes, in alginate composites or on large particles. For example, Dai et al. (2016) fabricated a laccase-carrying electrospun fibrous membrane by co-electrospinning a poly(D,L-lactide)/laccase/MWCNT mixture. The total removal (synergistic adsorption and degradation) of the target species (e.g., 2,4-dichlorophenol, bisphenol A, and triclosan) by the fabricated material reached 92.6, 95.5, and 99.7%, respectively, with 81.7, 90.5, and 85.6% contributions from the enzyme-catalyzed degradation of the respective contaminants (Dai et al., 2016). Li et al. (2010) immobilized CNTs by injecting a homogeneous dispersion of CNTs and sodium alginate into a solution of calcium chloride, with Ca^{2+} serving as the bridging agent. The authors successfully used the resulting material to remove Cu^{2+} from the water. Similarly, a composite fiber containing calcium alginate-MWCNT was obtained via wet spinning method, and the resulting material was used to remove dye compounds (both cationic and anionic) from aqueous media (Sui et al., 2012a). In a novel approach, MWCNTs were inserted into the cavities of diatomite and subsequently supported onto flexible polyurethane foams (Yu and Fugetsu, 2010). The composite material was able to effectively remove organic dye compounds from contaminated water (Yu and Fugetsu, 2010). In a similar approach, a sponge-like natural vermiculite-CNT hybrid was synthesized by intercalating CNTs into the exfoliated vermiculite for oil adsorption (Zhao et al., 2011). Several other clay minerals (e.g., smectite and palygorskite), which are naturally occurring, inexpensive, and non-toxic, have enormous potential to be developed as composite CNT adsorbents. The clay minerals themselves have well known environmental applications due to their high surface reactivity (Sarkar et al., 2012). Combining this feature with CNT composites is expected to promote the development of advanced environmental

adsorbents and simultaneously restrict the unwanted mobility of CNTs from the materials (Sarkar et al., 2015).

4.9. Modification with other carbon based adsorbents

Hybrid adsorbent materials containing CNTs as a major component have also been used to remove/treat environmental contaminants. A self-assembled graphene–CNT hybrid was prepared by autoclaving a mixed dispersion of pre-exfoliated graphene oxide and MWCNTs in ethanol/water (1:1 v/v) at 200 °C for 6 h (Ai and Jiang, 2012). Sui et al. (2012b) reported the synthesis of graphene–CNT hybrid aerogels in a green process, in which graphene oxide was reduced to graphene by Vitamin C in the presence of HCl. The authors (Sui et al., 2012b) synthesized hybrid aerogels by mixing graphene and MWCNTs under heat treatment and then drying the mixture with supercritical CO_2. Free-standing adsorbent papers were prepared from a mixture of different types of CNTs and graphene. These materials were then used successfully to adsorb both metal cations and nonpolar organic compounds (Dichiara et al., 2014b; 2015b). The prepared nanocomposites thus demonstrated up to four fold and 50% greater adsorption of Cu^{2+} from aqueous solutions than those of activated carbon and CNTs alone, respectively (Dichiara et al., 2015b). A similar material prepared from SWCNTs and graphene nanoplatelets exhibited 25% improvement in adsorption of organic contaminants (e.g., 1-pyrenebutyric acid, 2,4-dichlorophenoxyacetic acid, and diquat dibromide) in comparison with either component of the nanocomposites alone (Dichiara et al., 2014b). Similarly, CNT-biochar hybrid materials were prepared in two steps: (i) dip-coating of CNTs on a biochar feedstock in the presence or absence of a surfactant and (ii) slow pyrolysis of dip-coated dried feedstock (for 1 h at 600 °C) under an N_2 environment (Inyang et al., 2014; 2015). The loading of CNTs in these composites was arbitrary. Future research may focus on optimizing the mixing ratio of individual components to achieve the best adsorption of a target contaminant. Care should also be taken

to restrict the unwanted mobility of CNTs. The carbon-CNT hybrid material can also be magnetized by incorporating iron oxides. While Vadahanambi et al. (2013) used such a magnetic graphene-CNT hybrid material for removing arsenic from water, Wang et al. (2014) used it for adsorbing cationic dyes (i.e., methylene blue).

5. Contaminant treatment by CNTs

The key strategies for treating contaminants by CNTs mainly include adsorption and degradation/detoxification. In both cases, the reactivity of CNTs is often improved by modification or functionalization of the material. Designer CNTs can be prepared to target a specific contaminant element or compound for remediation. Designing CNTs with certain surface engineering may also facilitate the separation of the materials following the contaminant treatment process. **Fig. 5** depicts the potential avenues of CNT modification and their possible applications in environmental contaminant mitigation. The incorporation of a magnetic component into CNTs is one of the common approaches used for nanoparticle separation (Abdel Salam et al., 2012). With or without such modifications, CNTs have been reported to remediate several groups of contaminants, including emerging pollutants, phenolics, polycyclic aromatic hydrocarbons (PAHs), dyes, pesticides, chlorinated organics, and heavy metals. For example, Glomstad et al. (2016) reported that with decreasing oxygen-containing functional groups and increasing surface areas, SWCNTs and MWCNTs adsorbed a greater amount of phenanthrene in the presence of aqueous natural organic matter while significantly reducing the toxicity of the contaminant to freshwater algae *Pseudokirchneriella subcapitata*.

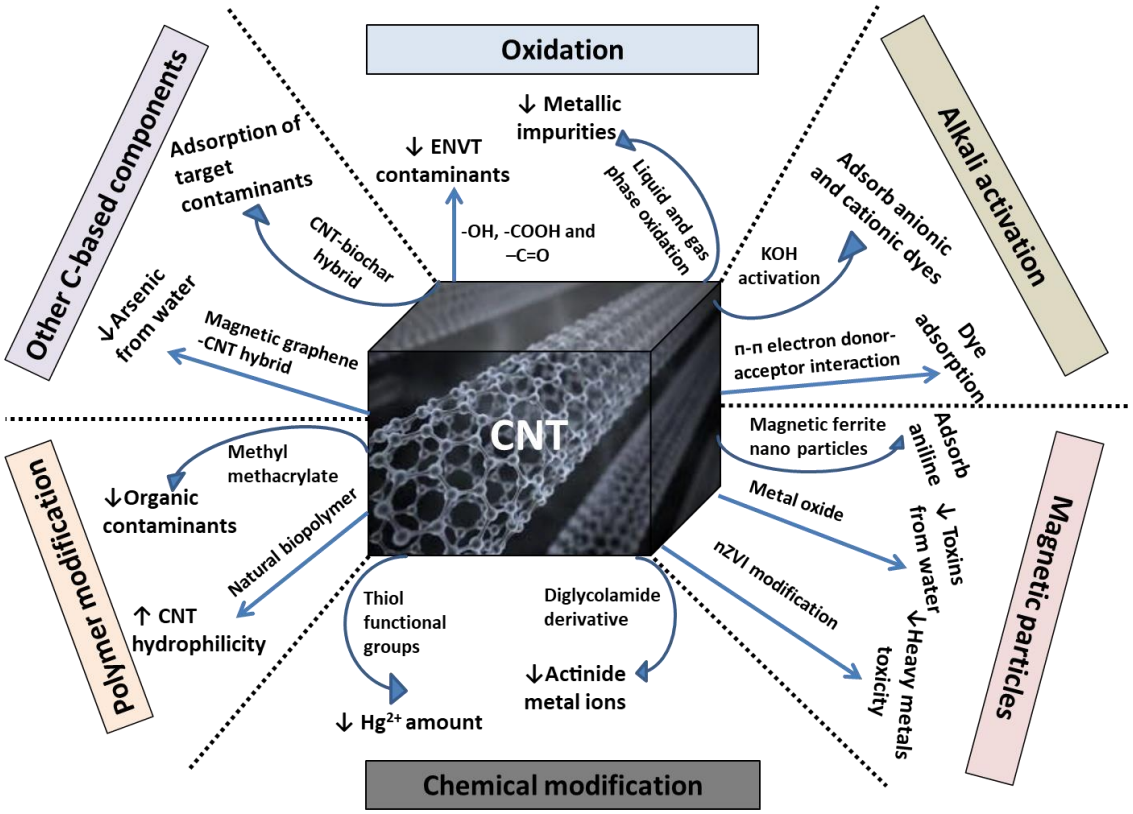


Fig. 5. Schematic diagram representing different modification processes of CNTs for contaminant removal from water and wastewater (*C: Carbon; CNT: Carbon nanotube; ENVT: Environmental; Hg: Mercury; KOH: Potassium hydroxide).*

5.1. Emerging contaminants

Modern manufacturing processes and industrial effluents discharge more than 80,000 synthetic chemicals into the environment every year (Naidu et al., 2016). Among the synthetic and naturally occurring chemicals, emerging contaminants are defined as those that have been newly observed in the environment. Tackling the issue of emerging contaminants is extremely challenging owing to the lack of (a) precise analytical methods for identifying contaminants, (b) certified reference materials for several of these chemicals, (c) information on their fate, toxicity, and behavior in the environment, (d) data of their environmental and human health limits, and (e) knowledge about their long-term (chronic) health impacts (Naidu and Wong,

587 2013; Naidu et al., 2016). Therefore, continuous efforts are needed to find effective materials
588 for cleaning up these contaminants.

589 Among emerging contaminants, pharmaceuticals and personal care products (PPCPs) are of
590 widespread public concern because their fate and mobility in the environment are largely
591 unknown (Yang et al., 2017). Some of the specific compounds in this group include ibuprofen
592 (an anti-inflammatory drug) and triclosan (5-chloro-2-(2,4-dichlorophenoxy)phenol, a
593 disinfectant). CNTs were successfully used to adsorb these compounds from aqueous media
594 (Cho et al., 2011). Given their large specific surface areas, SWCNTs showed better adsorption
595 of both ibuprofen and triclosan than MWCNTs. Oxidation of the CNT surface resulted in a
596 reduction of PPCP adsorption (Cho et al., 2011).

597 Many synthetic antibiotic compounds are considered to be emerging contaminants in the
598 environment. They are often only partially eliminated from the effluents of drug manufacturing
599 industries or public sewage systems. Therefore, a residual amount of these compounds can
600 reach the surface or groundwater. Although they can be present at low concentrations, such
601 small concentrations can also potentially develop resistance in soil and water microbial species.
602 When compared with an activated carbon and a synthetic carbon xerogel, an MWCNT sample
603 adsorbed almost the same amount of ciprofloxacin as activated carbon and about 40% less than
604 a xerogel (Carabineiro et al., 2011). Following a strong oxidation treatment (7 M HNO_3), the
605 adsorption capacities of the activated carbon and xerogel were drastically reduced, whereas the
606 adsorption by CNT was unaffected. However, a thermal treatment (900 °C) following the
607 oxidation enhanced the ciprofloxacin absorption performance of the activated carbon and
608 xerogel, but not that of the CNTs (Carabineiro et al., 2011). The combined oxidation and
609 thermal treatment increased the surface basicity of the materials and thus enhanced the
610 adsorption of the negatively charged antibiotic compound. Therefore, the removal of antibiotic

611 compounds by CNTs largely depends on the type of compounds themselves (cationic or
612 anionic).

613 The type of CNTs (whether single- or multi-walled) can significantly affect the material's
614 affinity for emerging contaminants. For example, the adsorption of perfluorooctane sulfonate
615 (PFOS) was greater for SWCNTs than for MWCNTs (Chen et al., 2011b). PFOS and
616 perfluorooctanoic acid (PFOA) are present in fire-extinguishing aqueous film-forming foam
617 (AFFF), and in recent years, they have emerged as some of the most concerning contaminants
618 because of their high concentration, wide global distribution, extremely high environmental
619 persistence, and potential for bioaccumulation (Arias Espana et al., 2015). CNTs demonstrated
620 a considerably fast adsorption equilibrium (as quick as 2 h) toward PFOS in comparison with
621 biomass-derived chars (384 h) and ash (48 h) because of the greater number of available
622 reaction sites in the cylindrical external surfaces of CNTs and the strong hydrophobic type
623 interaction mechanism (Chen et al., 2011b). Deng et al. (2012b) found that hydrophobic
624 interactions dominated the accumulation of perfluorinated compounds (PFCs) on CNTs. The
625 adsorption affinity of PFCs increased with the compounds' increasing C-F chain lengths, and
626 the functionalization of CNTs with oxygen-containing groups caused a reduction in PFC
627 adsorption (Deng et al., 2012b).

628 Among emerging inorganic contaminants, perchlorate (ClO_4^-) anions have received
629 widespread attention because of their disruptive effect on iodine uptake by mammals, which
630 leads to a number of diseases, such as thyroid disorder, neurological damage, and anemia
631 (Dasgupta et al., 2008; Sijimol et al., 2015). CNTs, especially the double-walled ones
632 (DWCNTs) with oxygen-containing functional groups, were found to remove perchlorate from
633 aqueous media (Fang and Chen, 2012). Perchlorate removal by various CNTs was in the order:
634 DWCNTs-oxidized > DWCNTs > SWCNTs > MWCNTs. Fang and Chen (2012) also
635 proposed a combined electrostatic interaction and hydrogen bonding mechanism for the

636 adsorption. However, these mechanisms should be further examined by conducting adsorption
637 tests under different pH values, ionic strengths, organic matter concentrations, and
638 temperatures.

639 Roxarsone (3-nitro-4-hydroxyphenylarsonic acid) is an organoarsenic compound used to
640 prevent and control parasites in poultry farming. The compound itself is not highly toxic, but
641 following degradation (which is quite fast under ambient environmental conditions), it can
642 produce extremely toxic inorganic arsenic species (Arai et al., 2003). Removal of roxarsone
643 using MWCNTs was evaluated by Hu et al. (2012). The authors suggested the suitability of
644 using MWCNTs for roxarsone remediation depending on both batch and static column test
645 results. The adsorption capacity reached 13.5 mg g^{-1}, which decreased markedly with rising
646 ionic strength and pH of the contaminant solutions. A π–π electron–donor–acceptor (EDA)
647 interaction was suggested to control the roxarsone adsorption reaction on the CNT surfaces
648 (Hu et al., 2012).

649 Magnetic particles decorated with surface-functionalized CNTs can also be used to
650 retain/concentrate emerging contaminants from aqueous media. For example, Guan et al.
651 (2010) used MWCNT functionalized magnetic particles to extract estrogen from solutions.
652 Indiscriminate disposal of medications is the main source of estrogen into the household
653 sewerage systems. As is apparent from the complex synthesis procedure of magnetic CNT
654 adsorbents (Guan et al., 2010), these materials may be inappropriate for treating high volumes
655 of contaminated wastewater owing to the high cost involved, but they can be efficient in
656 developing an analytical separation technique (separating media) for emerging contaminants.
657 A detection limit for diethylstilbestrol, estrone, and estriol estrogens as low as 0.2 ng mL^{-1} was
658 achieved by using a magnetically modified CNT material (Guan et al., 2010). **Table 1**
659 summarizes the examples of cases in which CNTs (with or without surface modification) were
660 used for removing various emerging contaminants from the environment.

661 **Table 1**

662 Removal of emerging contaminants by CNTs with or without surface modification.

CNT type	Modification	Target contaminant	Test method	Removal capacity	Remarks	Reference
SWCNTs and MWCNTs	Reflux with 70% w/w HNO_3	Ibuprofen (IBU) and triclosan (TCS)	Batch adsorption isotherm	For SWCNT, IBU at pH 7: 232 mg g^{-1}; TCS at pH 7: 558 mg g^{-1}	SWCNT adsorbed more IBU and TCS than MWCNT; IBU adsorption was greater at pH 4 whereas TCS adsorption was greater at pH 7; CNT surface oxidation reduced the adsorption.	(Cho et al., 2011)

MWCNTs	HNO_3 (7 M) oxidation and heat treatment (350 – 900 °C) under inert atmosphere (N_2)	Ciprofloxacin (CPX)	Batch adsorption isotherm and kinetics	About 150 mg g^{-1}	CNT adsorbed more CPX than activated carbon and carbon xerogel, but the oxidation and heat treatment did not impact the adsorption capacity of CNT.	(Carabineiro et al., 2011)
SWCNTs and MWCNTs	As received.	Perfluorooctane sulfonate (PFOS)	Batch adsorption kinetics	SWCNT: 237 mg g^{-1}	SWCNT adsorbed more PFOS than MWCNT.	(Chen et al., 2011b)
SWCNTs and MWCNTs	Functionalized by –OH and –COOH groups	Perfluorinated compounds (PFCs)	Batch adsorption isotherm	For SWCNT, Freundlich constants (K_F) for perfluorohexane acid,	SWCNT adsorbed more PFCs than MWCNT; adsorption	(Deng et al., 2012b)

				perfluorobutane acid, perfluorooctanoate, PFOS, perfluorobutane sulfonate and perfluorohexane sulfonate are 0.05, 0.07, 0.26, 1.61, 5.89 and 157, respectively.	increased with increasing C-F chain lengths; functionalization reduced adsorption.	
SWCNTs and MWCNTs	Reflux with 65% HNO3	Perchlorate (ClO_4^-)	Batch adsorption isotherm	As high as 3.55 mg g^{-1}	DWCNTs adsorbed more ClO_4^- than SWCNT and MWCNT; oxygen-containing functional groups improved adsorption.	(Fang and Chen, 2012)

MWCNTs	As received.	Roxarsone	Batch equilibrium adsorption and column adsorption	As high as 13.5 mg g^{-1}	Adsorption markedly decreased with increasing pH and ionic strength.	(Hu et al., 2012)
SWCNTs	In the presence of natural organic matter (NOM)	Bisphenol A (BPA) and 17β-estradiol (E2)	Batch adsorption and partition coefficient determination	Presence of NOM: 8 mg L^{-1} SWCNT: 10 mg L^{-1}	BPA and E2 adsorption ranged from 7.3% to 95% depending upon the solution pH and the absence and presence of NOM and SWCNTs	(Heo et al. 2012)

MWCNTs	Surface oxidized MWCNT containing 0.85, 2.16 and 7.07% oxygen	Atrazine [2-chloro-4-ethylamino-6-isopropylamino-s-triazine]	Adsorption kinetics, isotherm and thermodynamics	Pseudo second order model; adsorption of atrazine MWCNTs-O (0.85%): 17.35, MWCNTs-O (2.16%): 16.65 and MWCNTs-O (7.07%): 10.50 mg g^{-1}	Atrazine adsorption affinity decreased when the surface oxygen content increased	(Chen et al., 2009c)
MWCNTs	As prepared and oxidized	Diuron (pesticide)	Adsorption studies	Adsorption of diuron by As-prepared MWCNT: 28.37, and oxidized MWCNT: 29.82 mg g^{-1}	Diuron adsorption was pH dependent and favorable under neutral and basic conditions	(Deng et al., 2012a)

SWCNTs and MWCNTs	As received (presence of Cu^{2+})	Tetracycline	Batch adsorption studies	Freundlich coefficient for SWCNT: 1,150 and for MWCNT: 240 $mmol^{1-n} L^n kg^{-1}$	Tetracycline adsorption on MWCNTs (larger mesoporous interstices) was higher than SWCNT by the presence of Cu^{2+}	(Ji et al., 2010a)
MWCNTs	Coated with magnetic Fe_3O_4 followed by amino functionalization	Tetrabromobisphenol A	Batch adsorption studies	As high as 33.7 mg g^{-1}	The composite also adsorbed Pb(II) (75 mg g^{-1})	(Ji et al., 2012)

MWCNTs	Carboxyl functionalization	Mixture of four linear alkylbenzene sulfonates compounds	Batch adsorption studies	Up to 168 mg g^{-1}	Hydrophobic interaction and hydrogen bond formation enabled the adsorption	(Guan et al., 2017)

663

664 *5.2. Heavy metals, metalloids and radionuclides*

665 The affinity of CNTs towards heavy metals and metalloids was improved by oxidative
666 modification (Cho et al., 2010; Yu et al., 2011), incorporation of magnetic iron oxides (Chen
667 et al., 2009a; Addo Ntim and Mitra, 2011; Gupta et al., 2011a; Daneshvar Tarigh and
668 Shemirani, 2013), coating with non-magnetic metal oxides (Zhao et al., 2010), thiol
669 derivatization (Bandaru et al., 2013), and sulfur functionalization (Gupta et al., 2014). Among
670 the synthetic iron oxides, a mixture of goethite (α-FeO(OH)), hematite (α-Fe_2O_3), maghemite
671 (γ-Fe_2O_3), and magnetite (Fe_3O_4) was capable of removing trace quantities of heavy metal from
672 water (Addo Ntim and Mitra, 2011). The mechanism of heavy metal adsorption by CNT-based
673 materials is dependent on the employed modification/functionalization treatments (Gupta et
674 al., 2016; Ihsanullah et al., 2016). Generally, metal oxide-CNT composites adsorb heavy metals
675 and metalloids through a synergistic effect of chemisorption and physisorption (Addo Ntim
676 and Mitra, 2011). The adsorption affinity also highly depend on the ionic radius, hydration
677 energy, and hydrolysis potential of the specific contaminant element (Hu et al., 2011b). For
678 example, under similar experimental conditions, Pb(II) removal by iron oxide-coated
679 MWCNTs was greater than Cu(II) (Hu et al., 2011b). The presence of organic co-contaminants
680 also affected the adsorption of heavy metals by CNTs. For example, Cd(II) removal by
681 oxidized MWCNTs was enhanced by the coexistence of 1-naphthol, but the removal of 1-
682 naphthol was independent of the coexistence of Cd(II) in the same system (Yang et al., 2012a).
683 This result was mainly due to the difference in the adsorption mechanisms of the two
684 contaminants on functionalized MWCNTs. While high pH conditions may favor inner-sphere
685 complexation during metal adsorption, low pH may favor outer-sphere complexation and/or
686 ion exchange (Yang et al., 2012a). The adsorption of organic contaminants such as 1-naphthol
687 can take place through π–π bond formation between MWCNT structure and the contaminant's
688 aromatic rings (Yang et al., 2012a).

Similar to the mechanisms of heavy metal/metalloid removal, CNT-based materials were also reported to efficiently remediate various radionuclides. However, such studies are still rarely reported in the literature. **Table 2** lists the studies in which CNTs were used for heavy metal, metalloid, and radionuclide removal following various modifications/functionalizations. Despite the significant potential of using these modified/functionalized materials, no consensus has been reached with regard to the obtained results. For example, for the same heavy metal cation, different authors reported different removal capacities by employing specific modification processes. This indicates that extensive research is required and large-scale experiments should be conducted to confirm the results.

699 **Table 2**

700 Removal of heavy metals and radionuclides by CNTs with or without surface modification.

CNT type	Modification	Target contaminant	Test method	Removal capacity	Remarks	Reference
MWCNTs	Coated with iron oxide (Fe-MWCNT)	Trace level arsenic from drinking water	Kinetics and adsorption isotherm	As (III) and As (V) adsorption capacities of Fe-MWCNT were 1723 and 189 μg g^{-1}, respectively	Negatively charged As species may adsorb onto positively charged modified MWCNT sites	(Addo Ntim and Mitra, 2012)
SWCNTs	Thiol-derivatized SWCNT (SWCNT-SH) synthesized with HNO_3	Mercury, Hg (II)	Adsorption and desorption studies	Maximum Hg (II) adsorption with SWCNT-SH: 131 mg g^{-1}	Strong chemisorption between Hg (II) and thiol groups on derivatized SWCNT surfaces	(Bandaru et al., 2013)

MWCNTs	Iron oxide magnetic composite	Nickel [Ni(II)] and strontium [Sr(II)]	Batch adsorption studies	Ni(II) adsorption: ~80% (pH 8) and Sr(II) adsorption: ~95% (pH 10.4)	Ni(II) and Sr (II) on MECNT-iron oxide magnetic is highly dependent on pH. Ni(II) adsorption increased from 10% (pH 3.5) to 80% (pH 8.0)	(Chen et al., 2009a)
MWCNTs	Oxidation using chemical vapor deposition	Sr(II) and europium [Eu (III)]	Adsorption experiment	Sr(II) adsorption: ~36% and Eu(III) adsorption: ~96%	Increasing pH enhanced Sr(II) and Eu(III) adsorption, while increasing ionic strength decreased adsorption	(Chen et al., 2008)
MWCNTs	Diglycolamide functionalized MWCNT (DGA-MWCNTs)	Uranium from aqueous solution	Adsorption studies	Maximum Uranium adsorption by DGA-MWCNTs: 133.74 mg g^{-1}	Adsorption is favored at higher adsorbent concentration and higher temperature	(Deb et al., 2012)

MWCNTs	Oxidized with HNO_3	Cesium [Cs(I)] from aqueous solution	Batch method	About 13 mg g^{-1}	Low ionic strength, high pH and low initial Cs(I) concentration favored adsorption	(Yavari et al., 2011)
MWCNTs	Alumina coated CNT (Al_2O_3-MWCNT)	Lead ions from aqueous solution	Adsorption experiment	Al_2O_3-MWCNT increased lead absorption from 20% to 99% compared to MWCNTs	Lead adsorption increased when pH increased from 3 to 7	(Gupta et al., 2011b)
MWCNTs	Sulfur functionalized MWCNT with CS_2	Mercury [Hg(II)] from aqueous solution	Batch method	Maximum Hg(II) adsorption capacity by S-MWCNT: 151.5 mg g^{-1}	The material also effectively adsorbed Hg(0) vapor from CFL bulbs.	(Gupta et al., 2014)

MWCNTs	Magnetic nano-iron oxide coated MWCNT	Chromium [Cr(III)] from aqueous solution	Batch and fixed bed reactor	>90% Cr(III) removed from a 20 mg L^{-1} solution with 50 mg adsorbent at pH 6	In fixed bed mode, Cr(III) removal capacity increased with decreasing flow rate; the composite material performed better than activated carbon	(Gupta et al., 2011a)
MWCNTs	Magnetic iron oxide coated MWCNT	Lead [Pb(II)] and copper [Cu(II)] from wastewater	Batch method	Adsorption capacity of Pb(II): 10 – 31 mg g^{-1}; and Cu(II): 3 – 9 mg g^{-1}	Adsorption of metals depended on the ionic radius, hydration energies and hydrolysis of their hydroxides	(Hu et al., 2011b)
MWCNTs	Titanium dioxide (TiO_2) incorporated MWCNT	Lead [Pb(II)] from aqueous solution	Batch method	As high as 137 mg g^{-1}	Very fast and spontaneous adsorption	(Zhao et al., 2010)

MWCNTs	O_2-plasma-oxidized MWCNT	Lead [Pb(II)] from aqueous solution	Batch method	54 mg g^{-1}	Adsorption capacity was comparable to that of activated carbon	(Yu et al., 2011)
MWCNTs	Silver nanoparticles deposited MWCNT	Copper [Cu(II)] and cadmium [Cd(II)] from aqueous solution	Batch method	Cu(II): 58 mg g^{-1} Cd(II): 55 mg g^{-1}	Optimum adsorption of Cu(II) and Cd(II) was observed at pH 6 and 7, respectively	(Venkata Ramana et al., 2013)
MWCNTs	As received	Chromium [Cr(III)]	Batch method	2.07 mmol g^{-1}	Cr(III) is bound by surface carboxyl groups	(Manilo et al., 2017)

701

5.3. Organic dyes

Organic dye compounds are discharged into the environment from many industries (e.g., textile, cosmetics, and paper manufacturing processes). The wide occurrence of dyes in bodies of water raises concerns over their adverse effects on the ecosystem and human health. Compared with traditional adsorptive materials, CNTs exhibit remarkable affinity for organic dyes. Various CNT-based materials may be adopted for dye removal without further treatment (**Table 3)**.

710 **Table 3**

711 Treatment performance for the removal of selected dyes using different CNTs.

Dye contaminants	Adsorbent	Modification method	Surface area (m^2 g^{-1})	Capacity (q_m [a])/removal efficiency	References
Reactive blue 4; Acid red 183	MWCNTs	Untreated	217	69; 45	(Wang et al., 2012)
Acid blue 161	MWCNTs	Untreated	233	91.68%	(Geyikçi, 2013)
Acid red 18	MWCNTs	Untreated	270	166.67	(Shirmardi et al., 2012)
Alizarin red S; morin	MWCNTs	Untreated	NA [b]	161.29; 26.247	(Ghaedi et al., 2011)

Reactive blue 29	SWCNTs	Untreated	700	496	(Jahangiri-Rad et al., 2013)
Methyl orange	MWCNTs	Oxidized and microwave method	NA	306	(Mahmoodian et al., 2015)
Congo red	MWCNTs	Untreated	40	352.11	(Zare et al., 2015b)
Amido black 10B	MWCNTs	Functionalized by cysteamine composite (MWCNT-COOH-Cysteamine)	NA	131	(Sadegh et al., 2016)
Maxilon blue	MWCNTs	Untreated	NA	260.7	(Alkaim et al., 2015)
Methylene blue and neutral red	MWCNTs	Fe_2O_3 nanoparticles	114	MB: 42.3 and NR: 77.5	(Qu et al., 2008)

Congo red	MWCNTs	Impregnation with chitosan hydrogel beads	237.76	450.4	(Ruiz-Hitzky et al., 2011)
Direct red 23 (DR 23)	MWCNTs	Magnetic MWCNT Fe_3-C nanocomposites	38.7	85.5	(Yang et al., 2016)
Methylene blue and neutral red	MWCNTs	Grafted with guar gum (GG) and iron oxide nanoparticles	NA	MB: 61.92 NR: 89.85	(Yan et al., 2012b)
Reactive Red M-2BE	MWCNTs	Untreated	180.9	335.7	(Machado et al., 2011)
Acid blue 161 (AB 161)	MWCNTs	Untreated	233	458.33	(Ruiz-Garcia et al., 2013)
Reactive blue 4 (RB4) and acid red 183 (AR183)	MWCNTs	Untreated	217	RB4: 58.8 AR183: 45.3	(Wang et al., 2012)

Basic Red 46 (BR 46)	SWCNTs	Pristine and oxidized	~400	SWCNTs: 38.35 Oxidized: 49.45	(Moradi, 2013)
Reactive Red 120 (RR 120)	SWCNTs	Untreated	>700	426.49	(Walker et al., 2004)
Reactive blue 29 (RB 29)	SWCNTs	Untreated	700	496	(Dawson et al., 1998)
Malachite green	MWCNTs	Untreated	270	142.85	(Shirmardi et al., 2013)
Methylene blue, neutral red and brilliant cresyl blue	MWCNTs	Magnetic CNT-iron oxide composite	61.7	MB: 11.86 NR: 9.77 BCB: 6.28	(Gong et al., 2009)

Methyl orange and methylene blue	MWCNTs	Soluble starch coated magnetic iron oxide nanocomposite	132.6	MO: 135.6 MB: 93.7	(Chang et al., 2011)
Methylene blue	MWCNTs	Graphene-coated CNT hybrid using graphene oxide	78.9	87.97	(Ai and Jiang, 2012)

712

713 [a] q_m = maximum adsorption capacity (mg g^{-1}).

714 [b] NA = not available

715

716 Functionalization of CNTs can enhance adsorption ability of organic dyes (Zare et al.,
717 2015a). Among the various modification methods, oxidized MWCNTs are the most effective
718 in removing methylene orange and methylene blue from water matrixes (Ghaedi et al., 2012;
719 Mahmoodian et al., 2015). A new magnetic MWCNT-κ-carrageenan-Fe_3O_4 nanocomposite
720 was successfully prepared to effectively remove crystal violet (Duman et al., 2016). The new
721 nanocomposite can also be used in CNT modification to increase the adsorption capacity of
722 cationic dyes. Sadegh et al. (2016) showed that an adsorbent synthesized by CNT modification,
723 namely, MWCNT-COOH-cysteamine, could significantly enhance the removal of Amido
724 black 10B (AB 10B). The adsorption capacity of AB 10B using MWCNT-COOH and
725 MWCNT-COOH-cysteamine improved from 50.1 mg g^{-1} to 90 mg g^{-1} (80% increase) and 131
726 mg g^{-1} (162% increase), respectively. In addition, having large surface area, SWCNTs
727 demonstrated good adsorption properties. An excellent adsorption capacity of 496 mg g^{-1} was
728 obtained for the removal of Blue 29 (RB 29) (Jahangiri-Rad et al., 2013).
729
730 *5.4. Pesticides*
731 The widespread application of pesticides in agriculture has alarmingly contaminated our soil
732 and water resources. CNTs showed potential for effective removal of several types of pesticides
733 (**Table 4**). Deng et al. (2012a) reported that the adsorptive removal of diuron by as-prepared
734 and oxidized MWCNTs was most favored at pH ≥ 7.0. An oxidative modification of CNTs
735 increased the product's surface area and pore volume, which resulted in higher diuron removal
736 performance. The uptake of pesticides (chlordane and *p,p′*- dichlorodiphenyldichloroethylene)
737 in roots and shoots of lettuce crop was reduced by 88% and 78%, respectively, with the use of
738 non-functionalized CNTs, while the same were reduced by 57% and 23%, respectively, with
739 the use of amino-functionalized CNTs (Hamdi et al., 2015). Therefore, CNTs and their types
740 may significantly influence pesticide availability to plants. Investigations into electronically

741 sorted (i.e., semiconducting or metallic types) SWCNTs for the removal of 1-pyrenebutyric
742 acid, diquat dibromide and 2,4-dichlorophenoxyacetic acid from aqueous media revealed that
743 the semiconducting SWCNTs were capable of adsorbing up to 70.6% greater pesticides than
744 the metallic SWCNTs (Rocha et al., 2017). The lack of electron density around the
745 semiconducting SWCNTs would have favored high pesticide adsorption (Rocha et al., 2017).
746 By contrast, the adsorption of pesticides by CNTs is mostly restricted in batch systems, and
747 only a few studies have tested these materials in continuous flow experiments (Dichiara et al.,
748 2015a). The uptake of diquat dibromide in a fixed bed system by SWCNTs and MWCNTs was
749 not as high as in a batch system, but the former allowed the complete removal of the
750 contaminant over time (Dichiara et al., 2015a). Multiple mechanisms (i.e., hydrophobic
751 interaction, π–π binding, and micropore filling) were identified for the adsorption of diquat
752 dibromide by CNTs (Dichiara et al., 2015a). Thus far, information on pesticide removal with
753 the application of CNTs is not as extensive as the data on other organic contaminants.
754
755 **6. CNT-based water treatment technologies**
756 *6.1. Drinking water purification*
757 Compared with many conventional adsorbents commonly used in advanced water treatment
758 processes, CNTs have larger specific surface area. Generally SWCNTs hold a larger surface
759 area than MWCNTs. Surface oxygen content, which is another parameter that influences the
760 contaminant removal performance of CNTs, may be increased through oxidation process. The
761 adsorption capacity can also be increased up to 70% at an appropriate pH value. Enhanced
762 performance is also achieved with neutral PPCP molecules (e.g., triclosan and ibuprofen) than
763 their ionized forms (Wang et al., 2015). The presence of NOM and inorganic salts in the
764 influent may affect the adsorption process (Upadhyayula et al., 2009; Jung et al., 2015). In-
765 depth studies about detailed adsorption mechanisms of multi-pollutants, pilot or full-scale

766 operation of CNT processes, and commercial application of CNTs for drinking water
767 purification processes are still rare. Information on endocrine-disrupting compounds (EDCs)
768 and PPCPs adsorption using CNTs are inadequate as well (Ren et al., 2011). **Table 4**
769 summarizes the treatment performance of selected EDCs and PPCPs in either synthetic water
770 or water treatment plant effluent using different types of CNTs from recent studies. CNT
771 properties (e.g., surface area, charge, and functional groups) and operating parameters (e.g.,
772 pH, contact time, initial concentration, and temperature) play a vital role in determining the
773 treatment capacity of EDCs and PPCPs in CNT-based adsorption systems (Agnihotri et al.,
774 2006; Shi et al., 2010; Ahmed et al., 2012; Wang et al., 2015). Adsorption rate and capacity
775 were related to the physicochemical properties of organic pollutants (e.g., molecular size,
776 shape, hydrophobicity, and charge properties) (Cho et al., 2011; Joseph et al., 2011a; Ncibi and
777 Sillanpää, 2015). Wang et al. (2015) reported that SWCNTs and MWCNTs can effectively
778 remove triclosan, acetaminophen, and ibuprofen. However, in their study, the performance
779 ranged from approximately 10% to 95% owing to various factors. The removal efficiency
780 increased with increasing aromatic ring numbers in the compounds (e.g., ibuprofen < triclosan).

781 **Table 4**

782 Treatment performance for the removal of selected EDCs and PPCPs using different CNTs.

EDC and PPCP contaminants	Adsorbent	Surface area (m^2 g^{-1})	Source water	Capacity/removal efficiency/comment	References
Wide-spectrum antibiotics					
Ciprofloxacin	SWCNTs	576.7	Synthetic water	724 [a]	(Ncibi and Sillanpää, 2015)
Oxytetracycline	SWCNTs	576.7	Synthetic water	554 [a]	(Ncibi and Sillanpää, 2015)

Sulfadimethoxine	MWCNTs	174	Synthetic water	1300-1500 [b]	(Xia et al., 2013)
Sulfamethoxazole	MWCNTs	300	Synthetic water	10^2-10^3 [b]	(Ji et al., 2009)
Tylosin	MWCNTs	157-422	Synthetic water	11,300-33,900 [b]	(Ji et al., 2010b)
Ofloxacin	MWCNTs	117-228	Synthetic solution	80% adsorption	(Peng et al., 2012)
Norfloxacin	MWCNTs	160	Aqueous solution	84.7 [c]	(Yang et al., 2012b)
Sulfadimethoxine (SDM), sulfamethizole (SMZ),	MWCNTs	179	Aqueous solution	SDM: 9.68 [d] SMZ: 6.98 [d]	(Wei et al., 2017)

sulfamethazine (SMT) and sulfamethoxazole (SMX)				SMT: 1.25 [d] SMX: 1.53 [d]	
Hormones					
17-β-estradiol (E2)	SWCNTs	NA [e]	Synthetic water	115 [c]	(Zaib et al., 2012)
17α-ethinyl estradiol	SWCNTs	407	Synthetic water	35.6-35.7 [c]	(Joseph et al., 2011b)
Bisphenol A (BPA) and 17β-estradiol (E2)	SWCNTs	NA	Synthetic water	BPA: 122 [c]; E2: 162 [c]	(Heo et al., 2012)
Bisphenol A (BPA)	SWCNTs and MWCNTs	338-467	Synthetic wastewater	SWCNT: 55.5 [c] MWCNT: 19.4 [c]	(Renshaw et al., 2011)
NSAIDs [f]					

Diclofenac	MWCNTs	162	WTP effluent	22.3 [c]	(Sotelo et al., 2012)
Ibuprofen	SWCNTs and MWCNTs	1020,283	WTP effluent	10-95% removal	(Wang et al., 2015)
Bactericide/disinfectant					
Triclosan (TCS)	SWCNTs and MWCNTs	1020,283	WTP effluent	10-95% removal	(Wang et al., 2015)
Triclosan	MWCNTs	281	NA	157.7 [c]	(Navarro et al., 2008)
Triclosan	SWCNT	NA	NA	Triclosan interacts via chemical process with semiconductor (8,0) SWCNT, and via physical process with both	(Castro et al., 2017)

				semiconductor (8,0) and metallic (5,5) SWCNTs	
Pesticides/herbicides					
Isoproturon	MWCNTs	162	WTP effluent	8.1 [c]	(Sotelo et al., 2012)
Atrazine	SWCNTs	407	Synthetic water	4.97 [c]	(Jung et al., 2015)
Diuron	MWCNTs	258.6 to 427.5	Aqueous solution	As prepared: 42.6 [c] Oxidized: 49.2 [c]	(Deng et al., 2012a)
Dicholbenil	MWCNTs	83-558	Synthetic solution	17.5 [c]	(Chen et al., 2011a)

Phenoxy acid herbicide (4-chloro-2-methylphenoxyacetic acid)	SWCNTs	94-541	Synthetic solution	25.7 [c]	(Boularbah et al., 2006)
2,4-D	Regenerated SWCNT-graphene composite	NA	Aqueous solution	124 [c]	(Dichiara et al., 2014a)
Diquat dibromide	MWCNTs	233	Aqueous solution	83-87% [g]	(Dichiara et al., 2015a)
	SWCNTs	407		85-87% [g]	
	SWCNT-OH	407		57-61% [g]	

[a] Adsorption capacity from Brouers–Sotolongo model

[b] Distribution coefficient (L kg^{-1}) calculated from Freundlich model

[c] q_m = maximum adsorption capacity calculated from Langmuir model (mg g^{-1})

[d] K_F = Capacity factor (mg g^{-1})/(m^3 mg^{-1}) for Freundlich model

[e] NA = not available

[f] NSAIDs = Nonsteroidal anti-inflammatory drugs

[g] Utilization efficiency of the adsorbent in a fixed bed process

Biological contaminants are one of the major contaminants present in surface water and in water treatment plants (Upadhyayula et al., 2009; Smith and Rodrigues, 2015). The structural and functional properties of CNTs impart their highly affinitive interactions with biological contaminants. Compared with conventional adsorbents, CNTs possess superior bacterial inactivation efficiency and viral/bacterial spore adsorption capacity due to their larger surface areas (Lu and Su, 2007; Brady-Estévez et al., 2008). CNTs demonstrate immense potential in antimicrobial applications, particularly in drinking water purification (**Table 5**).

799 **Table 5**

800 Treatment performance for the removal of biological contaminants using different CNTs.

Biological contaminants	Adsorbent	Surface area (m^2 g^{-1})	Capacity/removal efficiency/comment	References
NOM				
DOC and AOC	SWCNTs	507	22–26 [a]	(Lu and Su, 2007)
Humic acid	CNTs	NA [b]	81-96 [a]	(Skandari et al., 2016)
Colloidal NOM and humic substances	SWCNTs	407	80-100%	(Ajmani et al., 2014)
Humic acid, Nordic lake fulvic acid, Waskish peat fulvic acid	MWCNTs	NA	10-40%	(Neiva et al., 2014)
Standard Suwannee River NOM (SR-NOM)	MWCNTs	NA	NOM adsorbed 0.033-0.104 mg C mg^{-1}	(Hyung et al., 2007)

Tannic acid (TA)	SWNCTs and MWCNTs	58-541	Adsorption of TA increased with decreasing CNT diameter	(Lin and Xing, 2008)
Trihalomethane (THM), dihaloacetonitrile (DHAN) and total N-nitrosamine (TONO) precursor	SWCNTs and MWCNTs	92-837	Adsorption varied with CNT type and dose, with TONO precursors having the highest percent removals (up to 97%)	(Needham et al., 2016)
Bacteria				
E. coli	SWCNTs	407	3.18 x 10^{12} CFU mL^{-1}	(Brady-Estévez et al., 2008)
E. coli and *B. subtilis*	PVK- SWCNTs	NA	>90% inactivation	(Ahmed et al., 2012)
E. coli DH5α	MWCNTs-Ag	NA	96% inactivation	(Su et al., 2013)
E. coli K12	SWCNTs	407	(79±9)% inactivation	(Brady-Estévez et al., 2008)

Streptococcus mutants	MWCNTs (surface modified)	250	Viable cells reduced by 7.5 log	(Bai et al., 2011)
Agrobacterium	MECNTs	88	Biodegradation efficiencies is 54.2%	(Xia et al., 2010)
Escherichia coli (*E.coli*) K12 and *Staphylococcus aureus* (*S.aureus*) SH 1000	SWCNTs	NA	CNT aggregation: 6.54×10^{-9} and 8.98×10^{-9} (*E. Coli*); 1.00×10^{-7} and 1.66×10^{-7} cm^2 s^{-1}	(Upadhyayula et al., 2008)
Viruses				
MS2 bacteriophage	SWCNTs	407	10^7-10^8 PFU mL^{-1}	(Brady-Estévez et al., 2008)
Influenza virus (H3N2)	CNTs	NA	detective limitation> 3.4 PFU mL^{-1}	(Ahmed et al., 2016)

MS2 bacteriophage	SWNCTs	407	10^6-10^7 PFU mL^{-1}	(Brady-Estévez et al., 2010)
MS2 bacteriophage (ATCC 15597-B1) along with host *E. Coli*	MWCNTs	NA	5.8 to 7.4 log inactivation	(Rahaman et al., 2012)
MS2 bacteriophage	SWCNTs	NA	9.3 and 9.8 PFU mL^{-1} limit detection	(Prieto-Simón et al., 2015)
Swine influenza virus (SIV) H1N1	SWCNTs	NA	Virus detection limit: 180 $TCID_{50}$ mL^{-1}	(Lottermoser, 2015)
Biological toxins				
Microcystin-LR	MWCNTs	NA	detective limitation 0.05-20 μg L^{-1}	(Han et al., 2013)

[a] q_m = Maximum adsorption capacity (mg g^{-1})

[b] NA = Not available

804 *6.2. Water desalination*

805 As a result of urban climate warming, the salinity levels of both land and sea water are
806 constantly increasing. Therefore, appropriate water desalination technologies should be
807 developed. CNTs, which feature low energy consumption and antimicrobial functions, have
808 been introduced for this application. In addition, CNTs can attract polar water molecules and
809 reject salts and pollutants (Goh et al., 2013). **Table 6** summarizes some successful cases of
810 membrane desalination processes employing CNTs.

Table 6

Desalination performance of different CNT membrane types (modified from Daer et al. (2015)).

CNT membrane type	Feed water	Operation conditions	Removal capacity	References
CNTs (forward osmosis)	0.58 M aqueous NaCl solution (feed), 1.74 M aqueous NaCl solution	300 K and 1 atm	100% salt rejection	(Jia et al., 2010)
MWCNT-COOH/ polyvinylidene fluoride	3.4% aqueous NaCl solution	24 mL min^{-1} feed flow, 1 L min^{-1} dry air in SGMD arrangement, 60–90 °C	99% salt rejection	(Bhadra et al., 2013)
Polyaniline polymer/SWCNT for capacitive deionization electrodes	100 μS cm^{-1} aqueous NaCl solution	20 mL min^{-1} feed flow rate, 1.2 V voltage	78.4% salt removal efficiency, 100% regeneration rate	(Yan et al., 2012a)

0.1% MWCNT/polyamide polymer	Aqueous NaCl solution	2000 mg L^{-1}, pH 7, 25 °C, transmembrane pressure 16 bar	28.05 L m^2 h water flux and N 90% salt rejection	(Zhao et al., 2014)
Polyethersulfone/0.045% MWCNT	200 mg L^{-1} each of Na_2SO_4, $MgSO_4$, and NaCl	4 bar, pH (7.0 ± 0.1), 25 ± 1 °C	Rejection of Na_2SO_4 (65%), $MgSO_4$ (45%), and NaCl (20%)	(Vatanpour et al., 2014)
MWCNT/polyethyleneimine-poly (amide–imide) hollow fiber forward osmosis	Deionized water (feed water)	0.5 M $MgCl_2$ solution (draw solution), 1 bar	87.8% $MgCl_2$ rejection	(Goh et al., 2013)
MWCNT/aromatic polyamide (PA) (15 mg MW-CNT/g PA)	Aqueous NaCl solution	(4000 ppm and 20 °C) 3.9 MPa	76% salt rejection	(Shawky et al., 2011)

MWCNT/carbonized nanofibrous membranes	Monochloroacetic acid (feed volume: 15 mL of 80 mg L^{-1})	Voltage: 14 to 18 kV and solution flow rate: 0.6 and 1.2 mL h^{-1}	Removal efficiency: 85%, rejection coefficient: 9%	(Asensio et al., 2013b)
Zwitterion functionalized CNT/polyamide nanocomposite membrane	1000 mg L^{-1} of Na^{+} (or ~2500 mg L^{-1} NaCl or 43.5 mM)	Water and ion flux pressure drop: 3.65 MPa (530 psi)	The rejection ratio is 20% for CNTs having five carboxylic acid groups	(Asensio et al., 2013a)
CNT-Bucky-papers/vacuum filtration in 99.8% pure propane-2-ol	Synthetic seawater (35 g L^{-1} NaCl solutions)	Hydrophobic membrane (contact angle 113˚), highly porous (90%), thermal conductivity of 2.7 kW m^{-2} h	99% salt rejection and a flux rate of ∼12 kg m^{-2} h	(Aciego Pietri and Brookes, 2009)
Polyvinyl chloride/MWCNT-co-copper nanolayer composite nanoparticles	0.5M NaCl solution	Flux: 6.10 (mol m^{-2} S) 10^{5} and electrical resistance: 19 Ω cm^{2}	Ionic permeability and flux increased from 0.5 to 8 wt% in prepared membrane	(Sanderson et al., 2015)

Vertically aligned-CNT (VA-CNT)	Colloidal silica, dextran, NaCl and Na_2SO_4	Pure water permeability for the VA-CNT 400 L m^{-2} h bar	The ratios of irreversible fouling to total resistance for VA-CNT: 68.8%	(Naidu, 2013)
CNT-film synthesized on macroporous surface of α-alumina support by chemical vapor deposition (CVD) of cyclohexanol and ferrocene	10,000, 20,000 and 30,000 mg L^{-1} of NaCl	Oxidized CNT membrane by HNO_3 and H_2SO_4 was very effective for salty water desalination	Maximum separation% was obtained at the highest feed concentration, temperature and flow rate (30,000 mg L^{-1}, 45 °C, and 500 L h^{-1}, respectively)	(Zanuzzi et al., 2009)
Honeycomb-CNT membrane (HC-CNT)	500 mM NaCl	CNT diameter had a marginal effect on the desalination of this new technology.	Increased salt rejection (95%) by applying an electric field of 0.8 V nm^{-1}.	(Castillejo and Castelló, 2010)

Carbon nanotube immobilized membrane (CNIM)	3.4 wt% NaCl solutions	Permeate flux reached up to 19.2 kg m^{-2} h for 3.4% NaCl concentration	More than 99% of the salt reduction was achieved, and the conductivity of the produced fresh water in the range of 1–2.5 μs cm^{-1}	(Abdelhafez et al., 2014)

813

Corry (2008) reported the size difference effect of CNT-based membranes on the performance of water desalination and developed models of the transport behavior of water molecules. The results showed that membranes comprising sub-nanometer diameter CNTs achieved a higher performance of water desalination when CNTs were used in reverse osmosis (RO). The use of hollow CNTs in membrane desalination with high removal performance was also reported (Goh et al., 2013). Water molecules can travel through CNT-based membranes without much impedance, which makes the membranes applicable under high flux conditions. The increased hydrophobicity of MWCNTs (e.g., functionalized polyamide polymer) can enable frictionless water migration across the membranes made of the nanotubes (Shawky et al., 2011; Zhao et al., 2014).

Modification of the CNT pores to selectively sense and reject contaminants can be achieved without even causing a significant damage to the inner surface characteristics of the nanotubes (Cohen-Tanugi and Grossman, 2012). A membrane developed by supporting oxidized CNTs on macroporous α-alumina was able to retain salinity-causing ions even at high temperatures (Tofighy et al., 2011). This could be achieved through the combined effects of ion retention and unimpeded water permeation across the CNT-membrane. The concentration of ions in the feed water may significantly influence the desalination efficiency of the membrane (Corry, 2011; Bhadra et al., 2013). However, owing to the easy water permeation property of the CNT-membrane, the effect of ion concentration may be largely overcome (Daer et al., 2015). In addition, specially-aligned CNTs may generate desirable channels in the membrane enabling a highly efficient desalination performance, and can act as “gatekeepers” for a size controlled separation process (Das et al., 2014). In terms of energy consumption, CNT membranes are a more cost-effective desalination technology than RO and forward osmosis (FO) (Fritzmann et al., 2007; Jia et al., 2010; Elimelech and Phillip, 2011; Goh et al., 2013). Despite its relatively

short research history, CNT-based desalination technologies are developing at a fast pace, and have seen many pilot to full-scale deployments in water treatment plants worldwide.

7. Interaction of CNTs with environmental colloids

Numerous environmental remediation technologies frequently require the remediation materials to be directly introduced into the contaminated soil, air, or water. At the same time, the behaviors of nano-sized engineered remediation materials in the environment are not fully known, and these materials can be harmful to the native ecology of the application site. This has sparked a debate as to whether CNTs are risk-free for remediation purposes. One can logically assume that CNT mobility through porous media (e.g., soil) may be restricted if they are grafted on large micro-particles (e.g., clay minerals). The clay minerals themselves are inert and naturally abundant in the environment.

Only a limited number of studies have investigated the role of environmental micro-nanoparticles such as clay minerals on the fate and availability of CNTs. The effect of clay minerals may largely depend on the type of surfactants used to obtain a stable suspension of CNTs. For example, MWCNT suspensions stabilized by cetyltrimethylammonium bromide were easily agglomerated by montmorillonite and kaolinite, whereas the same suspension stabilized by sodium dodecyl sulfate was unaffected by these clay minerals (Han et al., 2008). Two mechanisms were suggested to explain the effect of clay minerals on CNT agglomeration behaviors either when clay minerals removed the surfactants from the solution and the MWCNT surface or when surfactant molecules formed bridges between clay minerals and MWCNTs (Han et al., 2008). In a surfactant-free environment, the affinity of MWCNTs toward clay minerals followed the order of: smectite < kaolinite < shale under a given electrolyte concentration (Na^+) (Zhang et al., 2012). As the negative surface charge of smectite was greater than that of kaolinite, the latter imparted a lower repulsive force to the negatively charged

MWCNTs and more efficiently agglomerated them as compared to kaolinite (Zhang et al., 2012). By contrast, shale attracted CNTs through hydrophobic interactions due to the higher concentration of organic matter (Zhang et al., 2012). Environmental conditions (e.g., ionic strength) would significantly influence the above interactions. For example, a higher concentration of electrolytes or electrolytes with a higher valent cation would promote the rapid agglomeration of CNTs in the presence of any clay minerals (Saleh et al., 2008; Zhang et al., 2012; Schwyzer et al., 2013).

The interaction of CNTs with environmental macro or nanoparticles might also influence the former's adsorption capacity towards contaminant species. For example, Chen et al. (2017) recently reported that SiO_2 or Al_2O_3 nanoparticles inhibited the adsorption of sulfamethoxazole by MWCNTs. The increasing particle size of SiO_2 nanoparticles significantly affected sulfamethoxazole adsorption capacity, whereas Al_2O_3 provided a reverse effect in terms of their particle sizes (Chen et al., 2017). These results were probably due to the variable hetero-aggregation behavior of the nanoparticles with CNTs depending on their dissimilar surface change properties. Further research is needed to investigate the aggregation behavior of CNTs in the presence of different macro and nanoparticles in the environment so as to optimize their contaminant remediation ability.

8. Economic assessment

Cost can be an important obstacle to the practical applications of CNT-based materials for environmental remediation. Hundreds of thousands of liters of wastewater are produced every year, and thousands of hectares of soils are contaminated in various countries. Remediating such a huge volume of contaminated water and soil requires a large amount of CNTs. Some industrial-scale productions of CNTs have recently started, but this technology remains inaccessible to many environmental cleanup companies. Generally, MWCNTs are cheaper than

888 SWCNTs (Apul and Karanfil, 2015; Jia and Wei, 2017). The price of commercial CNTs falls
889 in the ranges of $0.6 to $25 per g of MWCNTs and $25 to $300 per g of SWCNTs depending
890 on the purity level and tube diameter of the products, as well as on the type of functionalization
891 undertaken in their preparation (www.cheaptubes.com; accessed on 07 May 2017). Thus,
892 MWCNTs are more frequently used than SWCNTs in environmental applications. However,
893 SWCNTs show better performance than MWCNTs in some environmental sensing
894 applications. MWCNTs might offer additional indirect benefits because they are usually less
895 toxic to non-target microorganisms in the environment than SWCNTs (Shrestha et al., 2013;
896 2015). Nonetheless, the development of technologies for large-scale production of high quality
897 CNTs (possibly from renewable carbon and catalyst precursors) (Gournis et al., 2002;
898 Bakandritsos et al., 2005; Su, 2009) requires further research to make CNT-based
899 environmental remediation technologies accessible. The cost of CNT-based water/wastewater
900 treatment technologies also depends on (i) the cost/complexity of CNT functionalization, (ii)
901 the type of water treatment (i.e., batch vs. continuous flow process), (iii) the need for
902 solid/liquid separation (e.g., magnetic CNTs can be easily recovered), and (iv) the recycling
903 cost and efficiency (i.e., CNTs typically exhibit higher regeneration capability). Contaminant
904 concentration in effluents can be one of the most critical factors in determining whether to
905 employ a batch or fixed bed treatment process to achieve an efficient and cost effective
906 treatment (Dichiara et al., 2015c). Empirical models can be used to choose the most appropriate
907 treatment process (either batch or fixed bed) that would minimize the adsorbent loading and
908 ultimately achieve the targeted removal of contaminants (Dichiara et al., 2015c). Further
909 research is needed to optimize the process parameters for cutting costs in CNT-based water
910 treatment technologies.
911
912 **9. Conclusions and future research direction**

CNTs exhibit excellent physicochemical, mechanical, thermal, and electrical properties that can be maximized for applications in environmental adsorbents, sensors, membranes, and catalysts. Designer CNTs, which are prepared through various functionalization or modification processes, demonstrate remarkable enhancement in contaminant removal efficiency and offer easy nanomaterial recovery and regeneration. CNTs can be functionalized/modified via oxidation, alkali activation, incorporation of magnetic properties, grafting of metal and metal oxide catalysts, hybridizing with other carbon nanomaterials, and derivatization with special chemical molecules. CNT-based materials can interact with diverse organic, inorganic, and biological contaminants, including heavy metals, radionuclides, pharmaceutical compounds, pesticides, dyes, hydrocarbons, and harmful microorganisms. The mechanism of contaminant removal through CNTs can be engineered in terms of their surface functionalization or modification type. In general, CNTs adsorb organic contaminants through hydrophobic interaction, π–π binding and micropore filling, and polar species through the formation of specific chemical bonds with the aid of surface functional groups and micropore filling. Some practical applications of CNTs in wastewater purification and desalination through membrane technology have been reported. However, the high cost of the materials, their complex interactions with environmental colloids and microorganisms, and the lack of pilot- and industrial-scale studies impede the widespread uptake of CNT-based water treatment technologies. The commercial acceptance of CNT in the environmental remediation industry might be improved by undertaking the following future research:

- More pilot- and large-scale studies to test the remediation performance of various CNT-based materials.
- Optimization of various process parameters for the application of CNT materials under diverse environmental conditions.
- Optimization of CNT modification and functionalization method.

- Development and testing of new CNT-based remediation technologies.
- Cost-effective synthesis of CNTs from renewable resources.

Acknowledgements

This work was supported by the National Research Foundation of Korea (NRF) grant funded by the Korea government (NRF-2015R1A2A2A11001432, Contribution: 100%). BS and SM acknowledge the Department of Education and Training, Australian Government, for awarding them the Endeavour Research Fellowship and Australian Post-graduate Award, respectively. This study is partly supported by 2015 Research Grant from Kangwon National University.

References

Abdel Salam, M., Gabal, M.A., Obaid, A.Y., 2012. Preparation and characterization of magnetic multi-walled carbon nanotubes/ferrite nanocomposite and its application for the removal of aniline from aqueous solution. Synthetic Metals 161, 2651-2658.

Abdelhafez, A.A., Li, J., Abbas, M.H.H., 2014. Feasibility of biochar manufactured from organic wastes on the stabilization of heavy metals in a metal smelter contaminated soil. Chemosphere 117, 66-71.

Aciego Pietri, J.C., Brookes, P.C., 2009. Substrate inputs and pH as factors controlling microbial biomass, activity and community structure in an arable soil. Soil Biology and Biochemistry 41, 1396-1405.

Addo Ntim, S., Mitra, S., 2011. Removal of trace arsenic to meet drinking water standards using iron oxide coated multiwall carbon nanotubes. Journal of Chemical and Engineering Data 56, 2077-2083.

961 Addo Ntim, S., Mitra, S., 2012. Adsorption of arsenic on multiwall carbon nanotube–zirconia
962 nanohybrid for potential drinking water purification. Journal of Colloid and Interface
963 Science 375, 154-159.
964 Agnihotri, S., Mota, J.P.B., Rostam-Abadi, M., Rood, M.J., 2006. Theoretical and
965 experimental investigation of morphology and temperature effects on adsorption of
966 organic vapors in single-walled carbon nanotubes. The Journal of Physical Chemistry
967 B 110, 7640-7647.
968 Ahmed, F., Santos, C.M., Vergara, R.A.M.V., Tria, M.C.R., Advincula, R., Rodrigues, D.F.,
969 2012. Antimicrobial applications of electroactive PVK-SWNT nanocomposites.
970 Environmental Science and Technology 46, 1804-1810.
971 Ahmed, S.R., Kim, J., Suzuki, T., Lee, J., Park, E.Y., 2016. Enhanced catalytic activity of
972 gold nanoparticle-carbon nanotube hybrids for influenza virus detection. Biosensors
973 and Bioelectronics 85, 503-508.
974 Ai, L., Jiang, J., 2012. Removal of methylene blue from aqueous solution with self-assembled
975 cylindrical graphene–carbon nanotube hybrid. Chemical Engineering Journal 192,
976 156-163.
977 Ajayan, P.M., 1999. Nanotubes from Carbon. Chemical Reviews 99, 1787-1800.
978 Ajayan, P.M., Ebbesen, T.W., Ichihashi, T., Iijima, S., Tanigaki, K., Hiura, H., 1993.
979 Opening carbon nanotubes with oxygen and implications for filling. Nature 362, 522-
980 525.
981 Ajmani, G.S., Cho, H.-H., Abbott Chalew, T.E., Schwab, K.J., Jacangelo, J.G., Huang, H.,
982 2014. Static and dynamic removal of aquatic natural organic matter by carbon
983 nanotubes. Water Research 59, 262-270.
984 Alkaim, A.F., Sadik, Z., Mahdi, D.K., Alshrefi, S.M., Al-Sammarraie, A.M., Alamgir, F.M.,
985 Singh, P.M., Aljeboree, A.M., 2015. Preparation, structure and adsorption properties

of synthesized multiwall carbon nanotubes for highly effective removal of maxilon blue dye. Korean Journal of Chemical Engineering 32, 2456-2462.

An, G., Ma, W., Sun, Z., Liu, Z., Han, B., Miao, S., Miao, Z., Ding, K., 2007. Preparation of titania/carbon nanotube composites using supercritical ethanol and their photocatalytic activity for phenol degradation under visible light irradiation. Carbon 45, 1795-1801.

Apul, O.G., Karanfil, T., 2015. Adsorption of synthetic organic contaminants by carbon nanotubes: A critical review. Water Research 68, 34-55.

Aqel, A., El-Nour, K.M.M.A., Ammar, R.A.A., Al-Warthan, A., 2012. Carbon nanotubes, science and technology part (I) structure, synthesis and characterisation. Arabian Journal of Chemistry 5, 1-23.

Arai, Y., Lanzirotti, A., Sutton, S., Davis, J.A., Sparks, D.L., 2003. Arsenic speciation and reactivity in poultry litter. Environmental Science and Technology 37, 4083-4090.

Arias Espana, V.A., Mallavarapu, M., Naidu, R., 2015. Treatment technologies for aqueous perfluorooctanesulfonate (PFOS) and perfluorooctanoate (PFOA): A critical review with an emphasis on field testing. Environmental Technology and Innovation 4, 168-181.

Asensio, V., Covelo, E.F., Kandeler, E., 2013a. Soil management of copper mine tailing soils — Sludge amendment and tree vegetation could improve biological soil quality. Science of The Total Environment 456–457, 82-90.

Asensio, V., Vega, F.A., Singh, B.R., Covelo, E.F., 2013b. Effects of tree vegetation and waste amendments on the fractionation of Cr, Cu, Ni, Pb and Zn in polluted mine soils. Science of The Total Environment 443, 446-453.

1009 Avilés, F., Cauich-Rodríguez, J.V., Moo-Tah, L., May-Pat, A., Vargas-Coronado, R., 2009.
1010 Evaluation of mild acid oxidation treatments for MWCNT functionalization. Carbon
1011 47, 2970-2975.
1012 Bai, Y., Park, I.S., Lee, S.J., Bae, T.S., Watari, F., Uo, M., Lee, M.H., 2011. Aqueous
1013 dispersion of surfactant-modified multiwalled carbon nanotubes and their application
1014 as an antibacterial agent. Carbon 49, 3663-3671.
1015 Bakandritsos, A., Simopoulos, A., Petridis, D., 2005. Carbon nanotube growth on a swellable
1016 clay matrix. Chemistry of Materials 17, 3468-3474.
1017 Bandaru, N.M., Reta, N., Dalal, H., Ellis, A.V., Shapter, J., Voelcker, N.H., 2013. Enhanced
1018 adsorption of mercury ions on thiol derivatized single wall carbon nanotubes. Journal
1019 of Hazardous Materials 261, 534-541.
1020 Baughman, R.H., Zakhidov, A.A., de Heer, W.A., 2002. Carbon nanotubes--the route toward
1021 applications. Science 297, 787-792.
1022 Bhadra, M., Roy, S., Mitra, S., 2013. Enhanced desalination using carboxylated carbon
1023 nanotube immobilized membranes. Separation and Purification Technology 120, 373-
1024 377.
1025 Bhatnagar, A., Sillanpää, M., 2010. Utilization of agro-industrial and municipal waste
1026 materials as potential adsorbents for water treatment—A review. Chemical
1027 Engineering Journal 157, 277-296.
1028 Bhatnagar, A., Vilar, V.J.P., Botelho, C.M.S., Boaventura, R.A.R., 2011. A review of the use
1029 of red mud as adsorbent for the removal of toxic pollutants from water and
1030 wastewater. Environmental Technology 32, 231-249.
1031 Boncel, S., Kyzioł-Komosińska, J., Krzyżewska, I., Czupioł, J., 2015. Interactions of carbon
1032 nanotubes with aqueous/aquatic media containing organic/inorganic contaminants and
1033 selected organisms of aquatic ecosystems – A review. Chemosphere 136, 211-221.

1034 Boularbah, A., Schwartz, C., Bitton, G., Morel, J.L., 2006. Heavy metal contamination from
1035 mining sites in South Morocco: 1. Use of a biotest to assess metal toxicity of tailings
1036 and soils. Chemosphere 63, 802-810.
1037 Brady-Estévez, A.S., Kang, S., Elimelech, M., 2008. A single-walled-carbon-nanotube filter
1038 for removal of viral and bacterial pathogens. Small 4, 481-484.
1039 Brady-Estévez, A.S., Nguyen, T.H., Gutierrez, L., Elimelech, M., 2010. Impact of solution
1040 chemistry on viral removal by a single-walled carbon nanotube filter. Water Research
1041 44, 3773-3780.
1042 Cañas, J.E., Long, M., Nations, S., Vadan, R., Dai, L., Luo, M., Ambikapathi, R., Lee, E.H.,
1043 Olszyk, D., 2008. Effects of functionalized and nonfunctionalized single-walled
1044 carbon nanotubes on root elongation of select crop species. Environmental
1045 Toxicology and Chemistry 27, 1922-1931.
1046 Carabineiro, S.A.C., Thavorn-Amornsri, T., Pereira, M.F.R., Figueiredo, J.L., 2011.
1047 Adsorption of ciprofloxacin on surface-modified carbon materials. Water Research
1048 45, 4583-4591.
1049 Castillejo, J.M., Castelló, R., 2010. Influence of the application rate of an organic amendment
1050 (Municipal Solid Waste [MSW] compost) on gypsum quarry rehabilitation in
1051 semiarid environments. Arid Land Research and Management 24, 344-364.
1052 Castro, S.M., Araújo, A.B., Nogueira, R.F.P., Guerini, S., 2017. Adsorption of triclosan on
1053 single wall carbon nanotubes: A first principle approach. Applied Surface Science
1054 403, 519-524.
1055 Chakrapani, N., Zhang, Y.M., Nayak, S.K., Moore, J.A., Carroll, D.L., Choi, Y.Y., Ajayan,
1056 P.M., 2003. Chemisorption of acetone on carbon nanotubes. The Journal of Physical
1057 Chemistry B 107, 9308-9311.

1058 Chang, P.R., Zheng, P., Liu, B., Anderson, D.P., Yu, J., Ma, X., 2011. Characterization of
1059 magnetic soluble starch-functionalized carbon nanotubes and its application for the
1060 adsorption of the dyes. Journal of Hazardous Materials 186, 2144-2150.
1061 Charlier, J.C., 2002. Defects in carbon nanotubes. Accounts of Chemical Research 35, 1063-
1062 1069.
1063 Chekli, L., Bayatsarmadi, B., Sekine, R., Sarkar, B., Shen, A.M., Scheckel, K.G., Skinner,
1064 W., Naidu, R., Shon, H.K., Lombi, E., Donner, E., 2016. Analytical characterisation
1065 of nanoscale zero-valent iron: A methodological review. Analytica Chimica Acta 903,
1066 13-35.
1067 Chen, B., Sun, W., Wang, C., Guo, X., 2017. Size-dependent impact of inorganic
1068 nanoparticles on sulfamethoxazole adsorption by carbon nanotubes. Chemical
1069 Engineering Journal 316, 160-170.
1070 Chen, C., Hu, J., Shao, D., Li, J., Wang, X., 2009a. Adsorption behavior of multiwall carbon
1071 nanotube/iron oxide magnetic composites for Ni(II) and Sr(II). Journal of Hazardous
1072 Materials 164, 923-928.
1073 Chen, C., Hu, J., Xu, D., Tan, X., Meng, Y., Wang, X., 2008. Surface complexation modeling
1074 of Sr(II) and Eu(III) adsorption onto oxidized multiwall carbon nanotubes. Journal of
1075 Colloid and Interface Science 323, 33-41.
1076 Chen, C.L., Wang, X.K., Nagatsu, M., 2009b. Europium adsorption on multiwall carbon
1077 nanotube/iron oxide magnetic composite in the presence of polyacrylic acid.
1078 Environmental Science and Technology 43, 2362-2367.
1079 Chen, G.-C., Shan, X.-Q., Pei, Z.-G., Wang, H., Zheng, L.-R., Zhang, J., Xie, Y.-N., 2011a.
1080 Adsorption of diuron and dichlobenil on multiwalled carbon nanotubes as affected by
1081 lead. Journal of Hazardous Materials 188, 156-163.

1082 Chen, G.-C., Shan, X.-Q., Zhou, Y.-Q., Shen, X.-e., Huang, H.-L., Khan, S.U., 2009c.
1083 Adsorption kinetics, isotherms and thermodynamics of atrazine on surface oxidized
1084 multiwalled carbon nanotubes. Journal of Hazardous Materials 169, 912-918.
1085 Chen, G., Qiu, J., Liu, Y., Jiang, R., Cai, S., Liu, Y., Zhu, F., Zeng, F., Luan, T., Ouyang, G.,
1086 2015. Carbon nanotubes act as contaminant carriers and translocate within plants.
1087 Scientific Reports 5, 15682.
1088 Chen, X., Xia, X., Wang, X., Qiao, J., Chen, H., 2011b. A comparative study on sorption of
1089 perfluorooctane sulfonate (PFOS) by chars, ash and carbon nanotubes. Chemosphere
1090 83, 1313-1319.
1091 Cho, H.-H., Huang, H., Schwab, K., 2011. Effects of solution chemistry on the adsorption of
1092 ibuprofen and triclosan onto carbon nanotubes. Langmuir 27, 12960-12967.
1093 Cho, H.-H., Wepasnick, K., Smith, B.A., Bangash, F.K., Fairbrother, D.H., Ball, W.P., 2010.
1094 Sorption of aqueous Zn[II] and Cd[II] by multiwall carbon nanotubes: The relative
1095 roles of oxygen-containing functional groups and graphenic carbon. Langmuir 26,
1096 967-981.
1097 Cohen-Tanugi, D., Grossman, J.C., 2012. Water desalination across nanoporous graphene.
1098 Nano Letters 12, 3602-3608.
1099 Collins, P.G., Bradley, K., Ishigami, M., Zettl, A., 2000. Extreme oxygen sensitivity of
1100 electronic properties of carbon nanotubes. Science 287, 1801-1804.
1101 Corry, B., 2008. Designing carbon nanotube membranes for efficient water desalination. The
1102 Journal of Physical Chemistry B 112, 1427-1434.
1103 Corry, B., 2011. Water and ion transport through functionalised carbon nanotubes:
1104 implications for desalination technology. Energy and Environmental Science 4, 751-
1105 759.

1106 Crane, R.A., Scott, T.B., 2012. Nanoscale zero-valent iron: Future prospects for an emerging
1107 water treatment technology. Journal of Hazardous Materials 211–212, 112-125.
1108 Daer, S., Kharraz, J., Giwa, A., Hasan, S.W., 2015. Recent applications of nanomaterials in
1109 water desalination: A critical review and future opportunities. Desalination 367, 37-
1110 48.
1111 Dai, Y., Yao, J., Song, Y., Wang, S., Yuan, Y., 2016. Enhanced adsorption and degradation
1112 of phenolic pollutants in water by carbon nanotube modified laccase-carrying
1113 electrospun fibrous membranes. Environmental Science: Nano 3, 857-868.
1114 Daneshvar Tarigh, G., Shemirani, F., 2013. Magnetic multi-wall carbon nanotube
1115 nanocomposite as an adsorbent for preconcentration and determination of lead (II)
1116 and manganese (II) in various matrices. Talanta 115, 744-750.
1117 Das, R., Ali, M.E., Hamid, S.B.A., Ramakrishna, S., Chowdhury, Z.Z., 2014. Carbon
1118 nanotube membranes for water purification: A bright future in water desalination.
1119 Desalination 336, 97-109.
1120 Dasgupta, P.K., Kirk, A.B., Dyke, J.V., Ohira, S.-I., 2008. Intake of iodine and perchlorate
1121 and excretion in human milk. Environmental Science and Technology 42, 8115-8121.
1122 Datsyuk, V., Kalyva, M., Papagelis, K., Parthenios, J., Tasis, D., Siokou, A., Kallitsis, I.,
1123 Galiotis, C., 2008. Chemical oxidation of multiwalled carbon nanotubes. Carbon 46,
1124 833-840.
1125 Dawson, R.F., Morgenstern, N.R., Stokes, A.W., 1998. Liquefaction flowslides in Rocky
1126 Mountain coal mine waste dumps. Canadian Geotechnical Journal 35, 328-343.
1127 de Oliveira, R., Hudari, F., Franco, J., Zanoni, M., 2015. Carbon nanotube-based
1128 electrochemical sensor for the determination of anthraquinone hair dyes in
1129 wastewaters. Chemosensors 3, 22.

1130 De Volder, M.F.L., Tawfick, S.H., Baughman, R.H., Hart, A.J., 2013. Carbon nanotubes:
1131 Present and future commercial applications. Science 339, 535-539.
1132 Deb, A.K.S., Ilaiyaraja, P., Ponraju, D., Venkatraman, B., 2012. Diglycolamide
1133 functionalized multi-walled carbon nanotubes for removal of uranium from aqueous
1134 solution by adsorption. Journal of Radioanalytical and Nuclear Chemistry 291, 877-
1135 883.
1136 Deng, J., Shao, Y., Gao, N., Deng, Y., Tan, C., Zhou, S., Hu, X., 2012a. Multiwalled carbon
1137 nanotubes as adsorbents for removal of herbicide diuron from aqueous solution.
1138 Chemical Engineering Journal 193–194, 339-347.
1139 Deng, S., Zhang, Q., Nie, Y., Wei, H., Wang, B., Huang, J., Yu, G., Xing, B., 2012b.
1140 Sorption mechanisms of perfluorinated compounds on carbon nanotubes.
1141 Environmental Pollution 168, 138-144.
1142 Dichiara, A.B., Benton-Smith, J., Rogers, R.E., 2014a. Enhanced adsorption of carbon
1143 nanocomposites exhausted with 2,4-dichlorophenoxyacetic acid after regeneration by
1144 thermal oxidation and microwave irradiation. Environmental Science: Nano 1, 113-
1145 116.
1146 Dichiara, A.B., Harlander, S.F., Rogers, R.E., 2015a. Fixed bed adsorption of diquat
1147 dibromide from aqueous solution using carbon nanotubes. RSC Advances 5, 61508-
1148 61512.
1149 Dichiara, A.B., Sherwood, T.J., Benton-Smith, J., Wilson, J.C., Weinstein, S.J., Rogers, R.E.,
1150 2014b. Free-standing carbon nanotube/graphene hybrid papers as next generation
1151 adsorbents. Nanoscale 6, 6322-6327.
1152 Dichiara, A.B., Webber, M.R., Gorman, W.R., Rogers, R.E., 2015b. Removal of copper ions
1153 from aqueous solutions via adsorption on carbon nanocomposites. ACS Applied
1154 Materials and Interfaces 7, 15674-15680.

1155 Dichiara, A.B., Weinstein, S.J., Rogers, R.E., 2015c. On the choice of batch or fixed bed
1156 adsorption processes for wastewater treatment. Industrial and Engineering Chemistry
1157 Research 54, 8579-8586.
1158 Duman, O., Tunç, S., Polat, T.G., Bozoğlan, B.K., 2016. Synthesis of magnetic oxidized
1159 multiwalled carbon nanotube-κ-carrageenan-Fe_3O_4 nanocomposite adsorbent and its
1160 application in cationic Methylene Blue dye adsorption. Carbohydrate Polymers 147,
1161 79-88.
1162 Elimelech, M., Phillip, W.A., 2011. The future of seawater desalination: Energy, technology,
1163 and the environment. Science 333, 712-717.
1164 Elliott, D.W., Zhang, W.-x., 2001. Field assessment of nanoscale bimetallic particles for
1165 groundwater treatment. Environmental Science and Technology 35, 4922-4926.
1166 Endo, M., Hayashi, T., Kim, Y.A., 2006. Large-scale production of carbon nanotubes and
1167 their applications. Pure and Applied Chemistry 78, 1703–1713.
1168 Ersan, G., Kaya, Y., Apul, O.G., Karanfil, T., 2016. Adsorption of organic contaminants by
1169 graphene nanosheets, carbon nanotubes and granular activated carbons under natural
1170 organic matter preloading conditions. Science of The Total Environment 565, 811-
1171 817.
1172 Eskandarian, L., Arami, M., Pajootan, E., 2014. Evaluation of adsorption characteristics of
1173 multiwalled carbon nanotubes modified by a poly(propylene imine) dendrimer in
1174 single and multiple dye solutions: Isotherms, kinetics, and thermodynamics. Journal
1175 of Chemical and Engineering Data 59, 444-454.
1176 Fang, Q., Chen, B., 2012. Adsorption of perchlorate onto raw and oxidized carbon nanotubes
1177 in aqueous solution. Carbon 50, 2209-2219.

1178 Foo, K.Y., Hameed, B.H., 2011. Preparation of oil palm (Elaeis) empty fruit bunch activated
1179 carbon by microwave-assisted KOH activation for the adsorption of methylene blue.
1180 Desalination 275, 302-305.
1181 Fritzmann, C., Löwenberg, J., Wintgens, T., Melin, T., 2007. State-of-the-art of reverse
1182 osmosis desalination. Desalination 216, 1-76.
1183 Fuhrer, R., Herrmann, I.K., Athanassiou, E.K., Grass, R.N., Stark, W.J., 2011. Immobilized
1184 β-cyclodextrin on surface-modified carbon-coated cobalt nanomagnets: Reversible
1185 organic contaminant adsorption and enrichment from water. Langmuir 27, 1924-1929.
1186 Garcia, J., Gomes, H.T., Serp, P., Kalck, P., Figueiredo, J.L., Faria, J.L., 2006. Carbon
1187 nanotube supported ruthenium catalysts for the treatment of high strength wastewater
1188 with aniline using wet air oxidation. Carbon 44, 2384-2391.
1189 Ge, B., Zhang, Z., Zhu, X., Ren, G., Men, X., Zhou, X., 2013. A magnetically
1190 superhydrophobic bulk material for oil removal. Colloids and Surfaces A:
1191 Physicochemical and Engineering Aspects 429, 129-133.
1192 Ge, J., Zhao, H.-Y., Zhu, H.-W., Huang, J., Shi, L.-A., Yu, S.-H., 2016. Advanced sorbents
1193 for oil-spill cleanup: Recent advances and future perspectives. Advanced Materials
1194 28, 10459-10490.
1195 Geyikçi, F., 2013. Adsorption of Acid Blue 161 (AB 161) dye from water by multi-walled
1196 carbon nanotubes. Fullerenes, Nanotubes and Carbon Nanostructures 21, 579-593.
1197 Ghaedi, M., Hassanzadeh, A., Kokhdan, S.N., 2011. Multiwalled carbon nanotubes as
1198 adsorbents for the kinetic and equilibrium study of the removal of Alizarin Red S and
1199 Morin. Journal of Chemical and Engineering Data 56, 2511-2520.
1200 Ghaedi, M., Khajehsharifi, H., Yadkuri, A.H., Roosta, M., Asghari, A., 2012. Oxidized
1201 multiwalled carbon nanotubes as efficient adsorbent for bromothymol blue.
1202 Toxicological and Environmental Chemistry 94, 873-883.

1203 Glomstad, B., Altin, D., Sørensen, L., Liu, J., Jenssen, B.M., Booth, A.M., 2016. Carbon
1204 nanotube properties influence adsorption of phenanthrene and subsequent
1205 bioavailability and toxicity to *Pseudokirchneriella subcapitata*. Environmental
1206 Science and Technology 50, 2660-2668.
1207 Goh, P.S., Ismail, A.F., Ng, B.C., 2013. Carbon nanotubes for desalination: Performance
1208 evaluation and current hurdles. Desalination 308, 2-14.
1209 Gong, J.-L., Wang, B., Zeng, G.-M., Yang, C.-P., Niu, C.-G., Niu, Q.-Y., Zhou, W.-J., Liang,
1210 Y., 2009. Removal of cationic dyes from aqueous solution using magnetic multi-wall
1211 carbon nanotube nanocomposite as adsorbent. Journal of Hazardous Materials 164,
1212 1517-1522.
1213 Gournis, D., Karakassides, M.A., Bakas, T., Boukos, N., Petridis, D., 2002. Catalytic
1214 synthesis of carbon nanotubes on clay minerals. Carbon 40, 2641-2646.
1215 Guan, Y., Jiang, C., Hu, C., Jia, L., 2010. Preparation of multi-walled carbon nanotubes
1216 functionalized magnetic particles by sol–gel technology and its application in
1217 extraction of estrogens. Talanta 83, 337-343.
1218 Guan, Z., Tang, X.-Y., Nishimura, T., Huang, Y.-M., Reid, B.J., 2017. Adsorption of linear
1219 alkylbenzene sulfonates on carboxyl modified multi-walled carbon nanotubes. Journal
1220 of Hazardous Materials 322, Part A, 205-214.
1221 Gui, X., Wei, J., Wang, K., Cao, A., Zhu, H., Jia, Y., Shu, Q., Wu, D., 2010. Carbon
1222 nanotube sponges. Advanced Materials 22, 617-621.
1223 Gui, X., Zeng, Z., Lin, Z., Gan, Q., Xiang, R., Zhu, Y., Cao, A., Tang, Z., 2013. Magnetic
1224 and highly recyclable macroporous carbon nanotubes for spilled oil sorption and
1225 separation. ACS Applied Materials and Interfaces 5, 5845-5850.

1226 Gupta, A., Vidyarthi, S.R., Sankararamakrishnan, N., 2014. Enhanced sorption of mercury
1227 from compact fluorescent bulbs and contaminated water streams using functionalized
1228 multiwalled carbon nanotubes. Journal of Hazardous Materials 274, 132-144.
1229 Gupta, S., Tai, N.-H., 2016. Carbon materials as oil sorbents: a review on the synthesis and
1230 performance. Journal of Materials Chemistry A 4, 1550-1565.
1231 Gupta, V.K., Agarwal, S., Saleh, T.A., 2011a. Chromium removal by combining the
1232 magnetic properties of iron oxide with adsorption properties of carbon nanotubes.
1233 Water Research 45, 2207-2212.
1234 Gupta, V.K., Agarwal, S., Saleh, T.A., 2011b. Synthesis and characterization of alumina-
1235 coated carbon nanotubes and their application for lead removal. Journal of Hazardous
1236 Materials 185, 17-23.
1237 Gupta, V.K., Karimi-Maleh, H., Sadegh, R., 2015. Simultaneous determination of
1238 hydroxylamine, phenol and sulfite in water and waste water samples using a
1239 voltammetric nanosensor. International Journal of Electrochemical Science 10, 303-
1240 316.
1241 Gupta, V.K., Kumar, R., Nayak, A., Saleh, T.A., Barakat, M.A., 2013. Adsorptive removal of
1242 dyes from aqueous solution onto carbon nanotubes: A review. Advances in Colloid
1243 and Interface Science 193–194, 24-34.
1244 Gupta, V.K., Moradi, O., Tyagi, I., Agarwal, S., Sadegh, H., Shahryari-Ghoshekandi, R.,
1245 Makhlouf, A.S.H., Goodarzi, M., Garshasbi, A., 2016. Study on the removal of heavy
1246 metal ions from industry waste by carbon nanotubes: Effect of the surface
1247 modification: a review. Critical Reviews in Environmental Science and Technology
1248 46, 93-118.
1249 Hadavifar, M., Bahramifar, N., Younesi, H., Li, Q., 2014. Adsorption of mercury ions from
1250 synthetic and real wastewater aqueous solution by functionalized multi-walled carbon

1251 nanotube with both amino and thiolated groups. Chemical Engineering Journal 237,
1252 217-228.
1253 Hamdi, H., De La Torre-Roche, R., Hawthorne, J., White, J.C., 2015. Impact of non-
1254 functionalized and amino-functionalized multiwall carbon nanotubes on pesticide
1255 uptake by lettuce (*Lactuca sativa* L.). Nanotoxicology 9, 172-180.
1256 Han, C., Doepke, A., Cho, W., Likodimos, V., de la Cruz, A.A., Back, T., Heineman, W.R.,
1257 Halsall, H.B., Shanov, V.N., Schulz, M.J., Falaras, P., Dionysiou, D.D., 2013. A
1258 multiwalled-carbon-nanotube-based biosensor for monitoring microcystin-LR in
1259 sources of drinking water supplies. Advanced Functional Materials 23, 1807-1816.
1260 Han, Z., Zhang, F., Lin, D., Xing, B., 2008. Clay minerals affect the stability of surfactant-
1261 facilitated carbon nanotube suspensions. Environmental Science and Technology 42,
1262 6869-6875.
1263 Harutyunyan, A.R., Chen, G., Paronyan, T.M., Pigos, E.M., Kuznetsov, O.A.,
1264 Hewaparakrama, K., Kim, S.M., Zakharov, D., Stach, E.A., Sumanasekera, G.U.,
1265 2009. Preferential growth of single-walled carbon nanotubes with metallic
1266 conductivity. Science 326, 116-120.
1267 Heo, J., Flora, J.R.V., Her, N., Park, Y.-G., Cho, J., Son, A., Yoon, Y., 2012. Removal of
1268 bisphenol A and 17β-estradiol in single walled carbon nanotubes–ultrafiltration
1269 (SWNTs–UF) membrane systems. Separation and Purification Technology 90, 39-52.
1270 Hu, J., Shao, D., Chen, C., Sheng, G., Li, J., Wang, X., Nagatsu, M., 2010. Plasma-induced
1271 grafting of cyclodextrin onto multiwall carbon nanotube/iron oxides for adsorbent
1272 application. The Journal of Physical Chemistry B 114, 6779-6785.
1273 Hu, J., Shao, D., Chen, C., Sheng, G., Ren, X., Wang, X., 2011a. Removal of 1-
1274 naphthylamine from aqueous solution by multiwall carbon nanotubes/iron
1275 oxides/cyclodextrin composite. Journal of Hazardous Materials 185, 463-471.

Hu, J., Tong, Z., Hu, Z., Chen, G., Chen, T., 2012. Adsorption of roxarsone from aqueous solution by multi-walled carbon nanotubes. Journal of Colloid and Interface Science 377, 355-361.

Hu, J., Zhao, D., Wang, X., 2011b. Removal of Pb(II) and Cu(II) from aqueous solution using multiwalled carbon nanotubes/iron oxide magnetic composites. Water Science and Technology 63, 917-923.

Huang, Y., Chen, X., 2014. Carbon nanomaterial-based composites in wastewater purification. Nano LIFE 04, 1441006.

Hylton, K., Chen, Y., Mitra, S., 2008. Carbon nanotube mediated microscale membrane extraction. Journal of Chromatography A 1211, 43-48.

Hyung, H., Fortner, J.D., Hughes, J.B., Kim, J.-H., 2007. Natural organic matter stabilizes carbon nanotubes in the aqueous phase. Environmental Science and Technology 41, 179-184.

Ihsanullah, Abbas, A., Al-Amer, A.M., Laoui, T., Al-Marri, M.J., Nasser, M.S., Khraisheh, M., Atieh, M.A., 2016. Heavy metal removal from aqueous solution by advanced carbon nanotubes: Critical review of adsorption applications. Separation and Purification Technology 157, 141-161.

Iijima, S., Ichihashi, T., 1993. Single-shell carbon nanotubes of 1-nm diameter. Nature 363, 603-605.

Inyang, M., Gao, B., Zimmerman, A., Zhang, M., Chen, H., 2014. Synthesis, characterization, and dye sorption ability of carbon nanotube–biochar nanocomposites. Chemical Engineering Journal 236, 39-46.

Inyang, M., Gao, B., Zimmerman, A., Zhou, Y., Cao, X., 2015. Sorption and cosorption of lead and sulfapyridine on carbon nanotube-modified biochars. Environmental Science and Pollution Research 22, 1868-1876.

1301 Jahangiri-Rad, M., Nadafi, K., Mesdaghinia, A., Nabizadeh, R., Younesian, M., Rafiee, M.,
1302 2013. Sequential study on reactive blue 29 dye removal from aqueous solution by
1303 peroxy acid and single wall carbon nanotubes: experiment and theory. Iranian Journal
1304 of Environmental Health Science and Engineering 10, 5-5.
1305 Jame Sadia, A., Zhou, Z., 2016. Electrochemical carbon nanotube filters for water and
1306 wastewater treatment. Nanotechnology Reviews, p. 41.
1307 Jamie, A., Alshami, A.S., Maliabari, Z.O., Ali Ateih, M., Al Hamouz, O.C.S., 2016.
1308 Immobilization and enhanced catalytic activity of lipase on modified MWCNT for
1309 oily wastewater treatment. Environmental Progress and Sustainable Energy 35, 1441-
1310 1449.
1311 Ji, L., Chen, W., Bi, J., Zheng, S., Xu, Z., Zhu, D., Alvarez, P.J., 2010a. Adsorption of
1312 tetracycline on single-walled and multi-walled carbon nanotubes as affected by
1313 aqueous solution chemistry. Environmental Toxicology and Chemistry 29, 2713-
1314 2719.
1315 Ji, L., Chen, W., Zheng, S., Xu, Z., Zhu, D., 2009. Adsorption of sulfonamide antibiotics to
1316 multiwalled carbon nanotubes. Langmuir 25, 11608-11613.
1317 Ji, L., Shao, Y., Xu, Z., Zheng, S., Zhu, D., 2010b. Adsorption of monoaromatic compounds
1318 and pharmaceutical antibiotics on carbon nanotubes activated by KOH etching.
1319 Environmental Science and Technology 44, 6429-6436.
1320 Ji, L., Zhou, L., Bai, X., Shao, Y., Zhao, G., Qu, Y., Wang, C., Li, Y., 2012. Facile synthesis
1321 of multiwall carbon nanotubes/iron oxides for removal of tetrabromobisphenol A and
1322 Pb(ii). Journal of Materials Chemistry 22, 15853-15862.
1323 Jia, X., Wei, F., 2017. Advances in production and applications of carbon nanotubes. Topics
1324 in Current Chemistry 375, 18.

1325 Jia, Y.-x., Li, H.-l., Wang, M., Wu, L.-y., Hu, Y.-d., 2010. Carbon nanotube: Possible
1326 candidate for forward osmosis. Separation and Purification Technology 75, 55-60.
1327 Jiao, W., Feng, Z., Liu, Y., Jiang, H., 2016. Degradation of nitrobenzene-containing
1328 wastewater by carbon nanotubes immobilized nanoscale zerovalent iron. Journal of
1329 Nanoparticle Research 18, 1-9.
1330 Jijun, Z., Alper, B., Jie, H., Jian Ping, L., 2002. Gas molecule adsorption in carbon nanotubes
1331 and nanotube bundles. Nanotechnology 13, 195.
1332 Joseph, L., Heo, J., Park, Y.-G., Flora, J.R.V., Yoon, Y., 2011a. Adsorption of bisphenol A
1333 and 17α-ethinyl estradiol on single walled carbon nanotubes from seawater and
1334 brackish water. Desalination 281, 68-74.
1335 Joseph, L., Zaib, Q., Khan, I.A., Berge, N.D., Park, Y.-G., Saleh, N.B., Yoon, Y., 2011b.
1336 Removal of bisphenol A and 17α-ethinyl estradiol from landfill leachate using single-
1337 walled carbon nanotubes. Water Research 45, 4056-4068.
1338 Jung, C., Son, A., Her, N., Zoh, K.-D., Cho, J., Yoon, Y., 2015. Removal of endocrine
1339 disrupting compounds, pharmaceuticals, and personal care products in water using
1340 carbon nanotubes: A review. Journal of Industrial and Engineering Chemistry 27, 1-
1341 11.
1342 Karimi-Maleh, H., Moazampour, M., Ensafi, A.A., Mallakpour, S., Hatami, M., 2014. An
1343 electrochemical nanocomposite modified carbon paste electrode as a sensor for
1344 simultaneous determination of hydrazine and phenol in water and wastewater
1345 samples. Environmental Science and Pollution Research 21, 5879-5888.
1346 Karwa, M., Iqbal, Z., Mitra, S., 2006. Scaled-up self-assembly of carbon nanotubes inside
1347 long stainless steel tubing. Carbon 44, 1235-1242.

1348 Kayvani Fard, A., McKay, G., Manawi, Y., Malaibari, Z., Hussien, M.A., 2016. Outstanding
1349 adsorption performance of high aspect ratio and super-hydrophobic carbon nanotubes
1350 for oil removal. Chemosphere 164, 142-155.
1351 Kazachkin, D., Nishimura, Y., Irle, S., Morokuma, K., Vidic, R.D., Borguet, E., 2008.
1352 Interaction of acetone with single wall carbon nanotubes at cryogenic temperatures: A
1353 combined temperature programmed desorption and theoretical study. Langmuir 24,
1354 7848-7856.
1355 Kuo, C.-Y., Lin, H.-Y., 2009. Adsorption of aqueous cadmium (II) onto modified multi-
1356 walled carbon nanotubes following microwave/chemical treatment. Desalination 249,
1357 792-796.
1358 Lee, C.H., Johnson, N., Drelich, J., Yap, Y.K., 2011. The performance of superhydrophobic
1359 and superoleophilic carbon nanotube meshes in water–oil filtration. Carbon 49, 669-
1360 676.
1361 Lee, J., Jeong, S., Liu, Z., 2016. Progress and challenges of carbon nanotube membrane in
1362 water treatment. Critical Reviews in Environmental Science and Technology 46, 999-
1363 1046.
1364 Li, Y., Liu, F., Xia, B., Du, Q., Zhang, P., Wang, D., Wang, Z., Xia, Y., 2010. Removal of
1365 copper from aqueous solution by carbon nanotube/calcium alginate composites.
1366 Journal of Hazardous Materials 177, 876-880.
1367 Liao, Q., Sun, J., Gao, L., 2009. Degradation of phenol by heterogeneous Fenton reaction
1368 using multi-walled carbon nanotube supported Fe2O3 catalysts. Colloids and Surfaces
1369 A: Physicochemical and Engineering Aspects 345, 95-100.
1370 Lin, D., Xing, B., 2008. Tannic acid adsorption and its role for stabilizing carbon nanotube
1371 suspensions. Environmental Science and Technology 42, 5917-5923.

1372 Liu, Y., Ba, H., Nguyen, D.-L., Ersen, O., Romero, T., Zafeiratos, S., Begin, D., Janowska, I.,
1373 Pham-Huu, C., 2013. Synthesis of porous carbon nanotubes foam composites with a
1374 high accessible surface area and tunable porosity. Journal of Materials Chemistry A 1,
1375 9508-9516.
1376 Liu, Y., Xie, J., Ong, C.N., Vecitis, C.D., Zhou, Z., 2015. Electrochemical wastewater
1377 treatment with carbon nanotube filters coupled with in situ generated H_2O_2.
1378 Environmental Science: Water Research and Technology 1, 769-778.
1379 Long, R.Q., Yang, R.T., 2001. Carbon nanotubes as superior sorbent for dioxin removal.
1380 Journal of the American Chemical Society 123, 2058-2059.
1381 Lottermoser, B.G., 2015. Rare earth elements in Australian uranium deposits. in: Merkel,
1382 B.J., Arab, A. (Eds.). Uranium - Past and Future Challenges: Proceedings of the 7th
1383 International Conference on Uranium Mining and Hydrogeology. Springer
1384 International Publishing, Switzerland, pp. 25-30.
1385 Lu, C., Su, F., 2007. Adsorption of natural organic matter by carbon nanotubes. Separation
1386 and Purification Technology 58, 113-121.
1387 Lv, X., Xu, J., Jiang, G., Xu, X., 2011. Removal of chromium(VI) from wastewater by
1388 nanoscale zero-valent iron particles supported on multiwalled carbon nanotubes.
1389 Chemosphere 85, 1204-1209.
1390 Ma, J., Yu, F., Zhou, L., Jin, L., Yang, M., Luan, J., Tang, Y., Fan, H., Yuan, Z., Chen, J.,
1391 2012. Enhanced adsorptive removal of methyl orange and methylene blue from
1392 aqueous solution by alkali-activated multiwalled carbon nanotubes. ACS Applied
1393 Materials and Interfaces 4, 5749-5760.
1394 Machado, F.M., Bergmann, C.P., Fernandes, T.H.M., Lima, E.C., Royer, B., Calvete, T.,
1395 Fagan, S.B., 2011. Adsorption of Reactive Red M-2BE dye from water solutions by

multi-walled carbon nanotubes and activated carbon. Journal of Hazardous Materials 192, 1122-1131.

Mahmoodian, H., Moradi, O., Shariatzadeha, B., Salehf, T.A., Tyagi, I., Maity, A., Asif, M., Gupta, V.K., 2015. Enhanced removal of methyl orange from aqueous solutions by poly HEMA–chitosan-MWCNT nano-composite. Journal of Molecular Liquids 202, 189-198.

Mandal, S., Sarkar, B., Bolan, N., Ok, Y.S., Naidu, R., 2017. Enhancement of chromate reduction in soils by surface modified biochar. Journal of Environmental Management 186, 277–284.

Manilo, M.V., Choma, Z.Z., Barany, S., 2017. Comparative study of Cr(III) adsorption by carbon nanotubes and active carbons. Colloid Journal 79, 212-218.

Mauter, M.S., Elimelech, M., 2008. Environmental applications of carbon-based nanomaterials. Environmental Science and Technology 42, 5843-5859.

Mishra, A.K., Arockiadoss, T., Ramaprabhu, S., 2010. Study of removal of azo dye by functionalized multi walled carbon nanotubes. Chemical Engineering Journal 162, 1026-1034.

Mishra, A.K., Ramaprabhu, S., 2010. Magnetite decorated multiwalled carbon nanotube based supercapacitor for arsenic removal and desalination of seawater. The Journal of Physical Chemistry C 114, 2583-2590.

Mohan, D., Sarswat, A., Ok, Y.S., Pittman Jr, C.U., 2014. Organic and inorganic contaminants removal from water with biochar, a renewable, low cost and sustainable adsorbent – A critical review. Bioresource Technology 160, 191-202.

Moradi, O., 2013. Adsorption behavior of basic red 46 by single-walled carbon nanotubes surfaces. Fullerenes, Nanotubes and Carbon Nanostructures 21, 286-301.

1420 Moradi, O., Yari, M., Zare, K., Mirza, B., Najafi, F., 2012. Carbon nanotubes: A review of
1421 chemistry principles and reactions. Fullerenes, Nanotubes and Carbon Nanostructures
1422 20, 138-151.
1423 Nagappan, S., Ha, C.-S., 2015. Emerging trends in superhydrophobic surface based magnetic
1424 materials: fabrications and their potential applications. Journal of Materials Chemistry
1425 A 3, 3224-3251.
1426 Nagasawa, S., Yudasaka, M., Hirahara, K., Ichihashi, T., Iijima, S., 2000. Effect of oxidation
1427 on single-wall carbon nanotubes. Chemical Physics Letters 328, 374-380.
1428 Naidu, R., 2013. Recent advances in contaminated site remediation. Water, Air and Soil
1429 Pollution 224, 1705.
1430 Naidu, R., Arias Espana, V.A., Liu, Y., Jit, J., 2016. Emerging contaminants in the
1431 environment: Risk-based analysis for better management. Chemosphere 154, 350-
1432 357.
1433 Naidu, R., Wong, M.H., 2013. Contaminants of emerging concern. Science of The Total
1434 Environment 463–464, 1077-1078.
1435 Navarro, M.C., Pérez-Sirvent, C., Martínez-Sánchez, M.J., Vidal, J., Tovar, P.J., Bech, J.,
1436 2008. Abandoned mine sites as a source of contamination by heavy metals: A case
1437 study in a semi-arid zone. Journal of Geochemical Exploration 96, 183-193.
1438 Ncibi, M.C., Sillanpää, M., 2015. Optimized removal of antibiotic drugs from aqueous
1439 solutions using single, double and multi-walled carbon nanotubes. Journal of
1440 Hazardous Materials 298, 102-110.
1441 Needham, E.M., Sidney, S.M., Chimka, J.R., Fairey, J.L., 2016. Trihalomethane,
1442 dihaloacetonitrile, and total N-nitrosamine precursor adsorption by carbon nanotubes:
1443 the importance of surface oxides and pore volume. Environmental Science: Water
1444 Research and Technology 2, 1004-1013.

1445 Neiva, A.M.R., Carvalho, P.C.S., Antunes, I.M.H.R., Silva, M.M.V.G., Santos, A.C.T.,
1446 Cabral Pinto, M.M.S., Cunha, P.P., 2014. Contaminated water, stream sediments and
1447 soils close to the abandoned Pinhal do Souto uranium mine, central Portugal. Journal
1448 of Geochemical Exploration 136, 102-117.
1449 Ok, Y.S., Chang, S.X., Gao, B., Chung, H.-J., 2015. SMART biochar technology—A shifting
1450 paradigm towards advanced materials and healthcare research. Environmental
1451 Technology and Innovation 4, 206-209.
1452 Patiño, Y., Díaz, E., Ordóñez, S., Gallegos-Suarez, E., Guerrero-Ruiz, A., Rodríguez-Ramos,
1453 I., 2015. Adsorption of emerging pollutants on functionalized multiwall carbon
1454 nanotubes. Chemosphere 136, 174-180.
1455 Peng, H., Pan, B., Wu, M., Liu, R., Zhang, D., Wu, D., Xing, B., 2012. Adsorption of
1456 ofloxacin on carbon nanotubes: Solubility, pH and cosolvent effects. Journal of
1457 Hazardous Materials 211–212, 342-348.
1458 Peng, X., Luan, Z., Ding, J., Di, Z., Li, Y., Tian, B., 2005. Ceria nanoparticles supported on
1459 carbon nanotubes for the removal of arsenate from water. Materials Letters 59, 399-
1460 403.
1461 Penza, M., Cassano, G., Aversa, P., Antolini, F., Cusano, A., Cutolo, A., Giordano, M.,
1462 Nicolais, L., 2004. Alcohol detection using carbon nanotubes acoustic and optical
1463 sensors. Applied Physics Letters 85, 2379-2381.
1464 Penza, M., Cassano, G., Rossi, R., Alvisi, M., Rizzo, A., Signore, M.A., Dikonimos, T.,
1465 Serra, E., Giorgi, R., 2007. Enhancement of sensitivity in gas chemiresistors based on
1466 carbon nanotube surface functionalized with noble metal (Au, Pt) nanoclusters.
1467 Applied Physics Letters 90, 173123.

1468 Perego, C., Bagatin, R., Tagliabue, M., Vignola, R., 2013. Zeolites and related mesoporous
1469 materials for multi-talented environmental solutions. Microporous and Mesoporous
1470 Materials 166, 37-49.
1471 Perreault, F., Fonseca de Faria, A., Elimelech, M., 2015. Environmental applications of
1472 graphene-based nanomaterials. Chemical Society Reviews 44, 5861-5896.
1473 Popov, V.N., 2004. Carbon nanotubes: properties and application. Materials Science and
1474 Engineering: R: Reports 43, 61-102.
1475 Prasek, J., Drbohlavova, J., Chomoucka, J., Hubalek, J., Jasek, O., Adam, V., Kizek, R.,
1476 2011. Methods for carbon nanotubes synthesis-review. Journal of Materials
1477 Chemistry 21, 15872-15884.
1478 Prieto-Simón, B., Bandaru, N.M., Saint, C., Voelcker, N.H., 2015. Tailored carbon nanotube
1479 immunosensors for the detection of microbial contamination. Biosensors and
1480 Bioelectronics 67, 642-648.
1481 Qu, S., Huang, F., Yu, S., Chen, G., Kong, J., 2008. Magnetic removal of dyes from aqueous
1482 solution using multi-walled carbon nanotubes filled with Fe_2O_3 particles. Journal of
1483 Hazardous Materials 160, 643-647.
1484 Rahaman, M.S., Vecitis, C.D., Elimelech, M., 2012. Electrochemical carbon-nanotube filter
1485 performance toward virus removal and inactivation in the presence of natural organic
1486 matter. Environmental Science and Technology 46, 1556-1564.
1487 Ramamurthy, S.S., Chen, Y., Kalyan, M.K., Rao, G.N., Chelli, J., Mitra, S., 2011. Carbon
1488 nanotube-zirconium dioxide hybrid for defluoridation of water. Journal of
1489 Nanoscience and Nanotechnology 11, 3552-3559.
1490 Rao, G.P., Lu, C., Su, F., 2007. Sorption of divalent metal ions from aqueous solution by
1491 carbon nanotubes: A review. Separation and Purification Technology 58, 224-231.

Ren, X., Chen, C., Nagatsu, M., Wang, X., 2011. Carbon nanotubes as adsorbents in environmental pollution management: A review. Chemical Engineering Journal 170, 395-410.

Ren, Z., Lan, Y., Wang, Y., 2013. Aligned carbon nanotubes: Physics, Concepts, Fabrication and Devices, 1st ed. Springer-Verlag Berlin Heidelberg.

Renshaw, J.C., Handley-Sidhu, S., Brookshaw, D.R., 2011. Chapter 7 Pathways of Radioactive Substances in the Environment. Nuclear Power and the Environment. The Royal Society of Chemistry, pp. 152-176.

Reza Sohrabi, M., Mansouriieh, N., Khosravi, M., Zolghadr, M., 2015. Removal of diazo dye Direct Red 23 from aqueous solution using zero-valent iron nanoparticles immobilized on multi-walled carbon nanotubes. Water Science and Technology 71, 1367-1374.

Rocha, J.-D.R., Rogers, R.E., Dichiara, A.B., Capasse, R.C., 2017. Emerging investigators series: highly effective adsorption of organic aromatic molecules from aqueous environments by electronically sorted single-walled carbon nanotubes. Environmental Science: Water Research and Technology 3, 203-212.

Ruiz-Garcia, C., Perez-Carvajal, J., Berenguer-Murcia, A., Darder, M., Aranda, P., Cazorla-Amoros, D., Ruiz-Hitzky, E., 2013. Clay-supported graphene materials: application to hydrogen storage. Physical Chemistry Chemical Physics 15, 18635-18641.

Ruiz-Hitzky, E., Darder, M., Fernandes, F.M., Zatile, E., Palomares, F.J., Aranda, P., 2011. Supported graphene from natural resources: Easy preparation and applications. Advanced Materials 23, 5250-5255.

Sadegh, H., Zare, K., Maazinejad, B., Shahryari-ghoshekandi, R., Tyagi, I., Agarwal, S., Gupta, V.K., 2016. Synthesis of MWCNT-COOH-cysteamine composite and its application for dye removal. Journal of Molecular Liquids 215, 221-228.

1517 Safavi, A., Maleki, N., Doroodmand, M.M., 2010. Fabrication of a selective mercury sensor
1518 based on the adsorption of cold vapor of mercury on carbon nanotubes: Determination
1519 of mercury in industrial wastewater. Journal of Hazardous Materials 173, 622-629.
1520 Saito, T., Matsushige, K., Tanaka, K., 2002. Chemical treatment and modification of multi-
1521 walled carbon nanotubes. Physica B: Condensed Matter 323, 280-283.
1522 Saleh, N.B., Pfefferle, L.D., Elimelech, M., 2008. Aggregation kinetics of multiwalled carbon
1523 nanotubes in aquatic systems: Measurements and environmental implications.
1524 Environmental Science and Technology 42, 7963-7969.
1525 Sanderson, P., Naidu, R., Bolan, N., 2015. Effectiveness of chemical amendments for
1526 stabilisation of lead and antimony in risk-based land management of soils of shooting
1527 ranges. Environmental Science and Pollution Research 22, 8942-8956.
1528 Santhosh, C., Velmurugan, V., Jacob, G., Jeong, S.K., Grace, A.N., Bhatnagar, A., 2016.
1529 Role of nanomaterials in water treatment applications: A review. Chemical
1530 Engineering Journal 306, 1116-1137.
1531 Sarkar, B., Liu, E., McClure, S., Sundaramurthy, J., Srinivasan, M., Naidu, R., 2015.
1532 Biomass derived palygorskite–carbon nanocomposites: Synthesis, characterisation
1533 and affinity to dye compounds. Applied Clay Science 114, 617-626.
1534 Sarkar, B., Xi, Y., Megharaj, M., Krishnamurti, G.S.R., Bowman, M., Rose, H., Naidu, R.,
1535 2012. Bioreactive organoclay: A new technology for environmental remediation.
1536 Critical Reviews in Environmental Science and Technology 42, 435-488.
1537 Schnorr, J.M., Swager, T.M., 2011. Emerging applications of carbon nanotubes. Chemistry of
1538 Materials 23, 646-657.
1539 Schwyzer, I., Kaegi, R., Sigg, L., Nowack, B., 2013. Colloidal stability of suspended and
1540 agglomerate structures of settled carbon nanotubes in different aqueous matrices.
1541 Water Research 47, 3910-3920.

1542 Shao, D., Chen, C., Wang, X., 2012. Application of polyaniline and multiwalled carbon
1543 nanotube magnetic composites for removal of Pb(II). Chemical Engineering Journal
1544 185–186, 144-150.
1545 Shao, D., Hu, J., Chen, C., Sheng, G., Ren, X., Wang, X., 2010. Polyaniline multiwalled
1546 carbon nanotube magnetic composite prepared by plasma-induced graft technique and
1547 its application for removal of aniline and phenol. The Journal of Physical Chemistry C
1548 114, 21524-21530.
1549 Shao, D., Hu, J., Jiang, Z., Wang, X., 2011. Removal of 4,4′-dichlorinated biphenyl from
1550 aqueous solution using methyl methacrylate grafted multiwalled carbon nanotubes.
1551 Chemosphere 82, 751-758.
1552 Shawky, H.A., Chae, S.-R., Lin, S., Wiesner, M.R., 2011. Synthesis and characterization of a
1553 carbon nanotube/polymer nanocomposite membrane for water treatment. Desalination
1554 272, 46-50.
1555 Sheng, G., Alsaedi, A., Shammakh, W., Monaquel, S., Sheng, J., Wang, X., Li, H., Huang,
1556 Y., 2016. Enhanced sequestration of selenite in water by nanoscale zero valent iron
1557 immobilization on carbon nanotubes by a combined batch, XPS and XAFS
1558 investigation. Carbon 99, 123-130.
1559 Shi, B., Zhuang, X., Yan, X., Lu, J., Tang, H., 2010. Adsorption of atrazine by natural
1560 organic matter and surfactant dispersed carbon nanotubes. Journal of Environmental
1561 Sciences 22, 1195-1202.
1562 Shi, L.-n., Zhang, X., Chen, Z.-l., 2011. Removal of Chromium (VI) from wastewater using
1563 bentonite-supported nanoscale zero-valent iron. Water Research 45, 886-892.
1564 Shirmardi, M., Mahvi, A.H., Hashemzadeh, B., Naeimabadi, A., Hassani, G., Niri, M.V.,
1565 2013. The adsorption of malachite green (MG) as a cationic dye onto functionalized

multi walled carbon nanotubes. Korean Journal of Chemical Engineering 30, 1603-1608.

Shirmardi, M., Mesdaghinia, A., Mahvi, A.H., Nasseri, S., Nabizadeh, R., 2012. Kinetics and equilibrium studies on adsorption of Acid Red 18 (azo-dye) using multiwall carbon nanotubes (MWCNTs) from aqueous solution. E-Journal of Chemistry 9.

Shrestha, B., Acosta-Martinez, V., Cox, S.B., Green, M.J., Li, S., Cañas-Carrell, J.E., 2013. An evaluation of the impact of multiwalled carbon nanotubes on soil microbial community structure and functioning. Journal of Hazardous Materials 261, 188-197.

Shrestha, B., Anderson, T.A., Acosta-Martinez, V., Payton, P., Cañas-Carrell, J.E., 2015. The influence of multiwalled carbon nanotubes on polycyclic aromatic hydrocarbon (PAH) bioavailability and toxicity to soil microbial communities in alfalfa rhizosphere. Ecotoxicology and Environmental Safety 116, 143-149.

Sijimol, M.R., Jyothy, S., Pradeepkumar, A.P., Chandran, M.S.S., Ghouse, S.S., Mohan, M., 2015. Review on fate, toxicity, and remediation of perchlorate. Environmental Forensics 16, 125-134.

Skandari, S., Torabian, A., Nabi Bidhendi, G., Baghdadi, M., Aminzadeh, B., 2016. Preparation of engineered carbon nanotube materials and its application in water treatment for removal of hydrophobic natural organic matter (NOM). Desalination and Water Treatment 57, 24855-24866.

Smith, S.C., Rodrigues, D.F., 2015. Carbon-based nanomaterials for removal of chemical and biological contaminants from water: A review of mechanisms and applications. Carbon 91, 122-143.

Sotelo, J.L., Rodríguez, A.R., Mateos, M.M., Hernández, S.D., Torrellas, S.A., Rodríguez, J.G., 2012. Adsorption of pharmaceutical compounds and an endocrine disruptor from

aqueous solutions by carbon materials. Journal of Environmental Science and Health, Part B 47, 640-652.

Stefaniuk, M., Oleszczuk, P., Ok, Y.S., 2016. Review on nano zerovalent iron (nZVI): From synthesis to environmental applications. Chemical Engineering Journal 287, 618-632.

Su, D.S., 2009. The use of natural materials in nanocarbon synthesis. ChemSusChem 2, 1009-1020.

Su, R., Jin, Y., Liu, Y., Tong, M., Kim, H., 2013. Bactericidal activity of Ag-doped multi-walled carbon nanotubes and the effects of extracellular polymeric substances and natural organic matter. Colloids and Surfaces B: Biointerfaces 104, 133-139.

Sud, D., Mahajan, G., Kaur, M.P., 2008. Agricultural waste material as potential adsorbent for sequestering heavy metal ions from aqueous solutions – A review. Bioresource Technology 99, 6017-6027.

Sui, K., Li, Y., Liu, R., Zhang, Y., Zhao, X., Liang, H., Xia, Y., 2012a. Biocomposite fiber of calcium alginate/multi-walled carbon nanotubes with enhanced adsorption properties for ionic dyes. Carbohydrate Polymers 90, 399-406.

Sui, Z., Meng, Q., Zhang, X., Ma, R., Cao, B., 2012b. Green synthesis of carbon nanotube-graphene hybrid aerogels and their use as versatile agents for water purification. Journal of Materials Chemistry 22, 8767-8771.

Tang, W.-W., Zeng, G.-M., Gong, J.-L., Liu, Y., Wang, X.-Y., Liu, Y.-Y., Liu, Z.-F., Chen, L., Zhang, X.-R., Tu, D.-Z., 2012. Simultaneous adsorption of atrazine and Cu (II) from wastewater by magnetic multi-walled carbon nanotube. Chemical Engineering Journal 211–212, 470-478.

Terranova, M.L., Sessa, V., Rossi, M., 2006. The world of carbon nanotubes: An overview of CVD growth methodologies. Chemical Vapor Deposition 12, 315-325.

1614 Thostenson, E.T., Ren, Z., Chou, T.-W., 2001. Advances in the science and technology of
1615 carbon nanotubes and their composites: a review. Composites Science and
1616 Technology 61, 1899-1912.
1617 Tofighy, M.A., Shirazi, Y., Mohammadi, T., Pak, A., 2011. Salty water desalination using
1618 carbon nanotubes membrane. Chemical Engineering Journal 168, 1064-1072.
1619 Tong, S., Zhao, S., Zhou, W., Li, R., Jia, Q., 2011. Modification of multi-walled carbon
1620 nanotubes with tannic acid for the adsorption of La, Tb and Lu ions. Microchimica
1621 Acta 174, 257-264.
1622 Tsang, S.C., Harris, P.J.F., Green, M.L.H., 1993. Thinning and opening of carbon nanotubes
1623 by oxidation using carbon dioxide. Nature 362, 520-522.
1624 Upadhyayula, V.K.K., Deng, S., Mitchell, M.C., Smith, G.B., 2009. Application of carbon
1625 nanotube technology for removal of contaminants in drinking water: A review.
1626 Science of The Total Environment 408, 1-13.
1627 Upadhyayula, V.K.K., Deng, S., Mitchell, M.C., Smith, G.B., Nair, V.K., Ghoshroy, S.,
1628 2008. Adsorption kinetics of *Escherichia coli* and *Staphylococcus aureus* on single-
1629 walled carbon nanotube aggregates. Water Science and Technology 58, 179-184.
1630 Üzüm, Ç., Shahwan, T., Eroğlu, A.E., Hallam, K.R., Scott, T.B., Lieberwirth, I., 2009.
1631 Synthesis and characterization of kaolinite-supported zero-valent iron nanoparticles
1632 and their application for the removal of aqueous Cu^{2+} and Co^{2+} ions. Applied Clay
1633 Science 43, 172-181.
1634 Vadahanambi, S., Lee, S.-H., Kim, W.-J., Oh, I.-K., 2013. Arsenic removal from
1635 contaminated water using three-dimensional graphene-carbon nanotube-iron oxide
1636 nanostructures. Environmental Science and Technology 47, 10510-10517.
1637 Vatanpour, V., Esmaeili, M., Farahani, M.H.D.A., 2014. Fouling reduction and retention
1638 increment of polyethersulfone nanofiltration membranes embedded by amine-

functionalized multi-walled carbon nanotubes. Journal of Membrane Science 466, 70-81.

Venkata Ramana, D.K., Yu, J.S., Seshaiah, K., 2013. Silver nanoparticles deposited multiwalled carbon nanotubes for removal of Cu(II) and Cd(II) from water: Surface, kinetic, equilibrium, and thermal adsorption properties. Chemical Engineering Journal 223, 806-815.

Vithanage, M., Seneviratne, M., Ahmad, M., Sarkar, B., Ok, Y.S., 2017. Contrasting effects of engineered carbon nanotubes on plants: a review. Environmental Geochemistry and Health, doi:10.1007/s10653-017-9957-y.

Vuković, G.D., Marinković, A.D., Čolić, M., Ristić, M.Đ., Aleksić, R., Perić-Grujić, A.A., Uskoković, P.S., 2010. Removal of cadmium from aqueous solutions by oxidized and ethylenediamine-functionalized multi-walled carbon nanotubes. Chemical Engineering Journal 157, 238-248.

Vuković, G.D., Marinković, A.D., Škapin, S.D., Ristić, M.Đ., Aleksić, R., Perić-Grujić, A.A., Uskoković, P.S., 2011. Removal of lead from water by amino modified multi-walled carbon nanotubes. Chemical Engineering Journal 173, 855-865.

Walker, D.J., Clemente, R., Bernal, M.P., 2004. Contrasting effects of manure and compost on soil pH, heavy metal availability and growth of *Chenopodium album* L. in a soil contaminated by pyritic mine waste. Chemosphere 57, 215-224.

Wang, H., Wang, H.-L., Jiang, W.-F., 2009a. Solar photocatalytic degradation of 2,6-dinitro-p-cresol (DNPC) using multi-walled carbon nanotubes (MWCNTs)–TiO_2 composite photocatalysts. Chemosphere 75, 1105-1111.

Wang, H., Wang, H.-L., Jiang, W.-F., Li, Z.-Q., 2009b. Photocatalytic degradation of 2,4-dinitrophenol (DNP) by multi-walled carbon nanotubes (MWCNTs)/TiO_2 composite in aqueous solution under solar irradiation. Water Research 43, 204-210.

1664 Wang, P., Cao, M., Wang, C., Ao, Y., Hou, J., Qian, J., 2014. Kinetics and thermodynamics
1665 of adsorption of methylene blue by a magnetic graphene-carbon nanotube composite.
1666 Applied Surface Science 290, 116-124.
1667 Wang, Q., Li, J., Chen, C., Ren, X., Hu, J., Wang, X., 2011. Removal of cobalt from aqueous
1668 solution by magnetic multiwalled carbon nanotube/iron oxide composites. Chemical
1669 Engineering Journal 174, 126-133.
1670 Wang, S., Ng, C.W., Wang, W., Li, Q., Li, L., 2012. A comparative study on the adsorption
1671 of acid and reactive dyes on multiwall carbon nanotubes in single and binary dye
1672 systems. Journal of Chemical and Engineering Data 57, 1563-1569.
1673 Wang, W., Zhou, M., Mao, Q., Yue, J., Wang, X., 2010. Novel NaY zeolite-supported
1674 nanoscale zero-valent iron as an efficient heterogeneous fenton catalyst. Catalysis
1675 Communications 11, 937-941.
1676 Wang, Y., Zhu, J., Huang, H., Cho, H.-H., 2015. Carbon nanotube composite membranes for
1677 microfiltration of pharmaceuticals and personal care products: Capabilities and
1678 potential mechanisms. Journal of Membrane Science 479, 165-174.
1679 Wei, J., Sun, W., Pan, W., Yu, X., Sun, G., Jiang, H., 2017. Comparing the effects of
1680 different oxygen-containing functional groups on sulfonamides adsorption by carbon
1681 nanotubes: Experiments and theoretical calculation. Chemical Engineering Journal
1682 312, 167-179.
1683 Wepasnick, K.A., Smith, B.A., Bitter, J.L., Howard Fairbrother, D., 2010. Chemical and
1684 structural characterization of carbon nanotube surfaces. Analytical and Bioanalytical
1685 Chemistry 396, 1003-1014.
1686 Woan, K., Pyrgiotakis, G., Sigmund, W., 2009. Photocatalytic carbon-nanotube–TiO_2
1687 composites. Advanced Materials 21, 2233-2239.

1688 Xia, M., Li, A., Zhu, Z., Zhou, Q., Yang, W., 2013. Factors influencing antibiotics adsorption
1689 onto engineered adsorbents. Journal of Environmental Sciences 25, 1291-1299.
1690 Xia, X., Li, Y., Zhou, Z., Feng, C., 2010. Bioavailability of adsorbed phenanthrene by black
1691 carbon and multi-walled carbon nanotubes to *Agrobacterium*. Chemosphere 78, 1329-
1692 1336.
1693 Xu, J., Lv, X., Li, J., Li, Y., Shen, L., Zhou, H., Xu, X., 2012. Simultaneous adsorption and
1694 dechlorination of 2,4-dichlorophenol by Pd/Fe nanoparticles with multi-walled carbon
1695 nanotube support. Journal of Hazardous Materials 225–226, 36-45.
1696 Yan, C., Zou, L., Short, R., 2012a. Single-walled carbon nanotubes and polyaniline
1697 composites for capacitive deionization. Desalination 290, 125-129.
1698 Yan, L., Chang, P.R., Zheng, P., Ma, X., 2012b. Characterization of magnetic guar gum-
1699 grafted carbon nanotubes and the adsorption of the dyes. Carbohydrate Polymers 87,
1700 1919-1924.
1701 Yang, S., Guo, Z., Sheng, G., Wang, X., 2012a. Investigation of the sequestration
1702 mechanisms of Cd(II) and 1-naphthol on discharged multi-walled carbon nanotubes in
1703 aqueous environment. Science of The Total Environment 420, 214-221.
1704 Yang, S., Wu, P., Chen, L., Li, L., Huang, Z., Liu, S., Li, L., 2016. A facile method to
1705 fabricate N-doped graphene-like carbon as efficient electrocatalyst using spent
1706 montmorillonite. Applied Clay Science 132–133, 731-738.
1707 Yang, W., Lu, Y., Zheng, F., Xue, X., Li, N., Liu, D., 2012b. Adsorption behavior and
1708 mechanisms of norfloxacin onto porous resins and carbon nanotube. Chemical
1709 Engineering Journal 179, 112-118.
1710 Yang, Y., Ok, Y.S., Kim, K.-H., Kwon, E.E., Tsang, Y.F., 2017. Occurrences and removal of
1711 pharmaceuticals and personal care products (PPCPs) in drinking water and

water/sewage treatment plants: A review. Science of The Total Environment 596–597, 303-320.

Yavari, R., Huang, Y.D., Ahmadi, S.J., 2011. Adsorption of cesium (I) from aqueous solution using oxidized multiwall carbon nanotubes. Journal of Radioanalytical and Nuclear Chemistry 287, 393-401.

Yu, F., Wu, Y., Li, X., Ma, J., 2012. Kinetic and thermodynamic studies of toluene, ethylbenzene, and m-xylene adsorption from aqueous solutions onto KOH-activated multiwalled carbon nanotubes. Journal of Agricultural and Food Chemistry 60, 12245-12253.

Yu, H., Fugetsu, B., 2010. A novel adsorbent obtained by inserting carbon nanotubes into cavities of diatomite and applications for organic dye elimination from contaminated water. Journal of Hazardous Materials 177, 138-145.

Yu, J.-G., Zhao, X.-H., Yang, H., Chen, X.-H., Yang, Q., Yu, L.-Y., Jiang, J.-H., Chen, X.-Q., 2014. Aqueous adsorption and removal of organic contaminants by carbon nanotubes. Science of The Total Environment 482–483, 241-251.

Yu, X.-Y., Luo, T., Zhang, Y.-X., Jia, Y., Zhu, B.-J., Fu, X.-C., Liu, J.-H., Huang, X.-J., 2011. Adsorption of lead(II) on O_2-plasma-oxidized multiwalled carbon nanotubes: Thermodynamics, kinetics, and desorption. ACS Applied Materials and Interfaces 3, 2585-2593.

Zaib, Q., Khan, I.A., Saleh, N.B., Flora, J.R.V., Park, Y.-G., Yoon, Y., 2012. Removal of bisphenol A and 17β-estradiol by single-walled carbon nanotubes in aqueous solution: Adsorption and molecular modeling. Water, Air, and Soil Pollution 223, 3281-3293.

Zanuzzi, A., Arocena, J.M., van Mourik, J.M., Faz Cano, A., 2009. Amendments with organic and industrial wastes stimulate soil formation in mine tailings as revealed by micromorphology. Geoderma 154, 69-75.

1737 Zare, K., Gupta, V.K., Moradi, O., Makhlouf, A.S.H., Sillanpää, M., Nadagouda, M.N.,
1738 Sadegh, H., Shahryari-ghoshekandi, R., Pal, A., Wang, Z.-j., Tyagi, I., Kazemi, M.,
1739 2015a. A comparative study on the basis of adsorption capacity between CNTs and
1740 activated carbon as adsorbents for removal of noxious synthetic dyes: a review.
1741 Journal of Nanostructure in Chemistry 5, 227-236.
1742 Zare, K., Sadegh, H., Shahryari-ghoshekandi, R., Maazinejad, B., Ali, V., Tyagi, I., Agarwal,
1743 S., Gupta, V.K., 2015b. Enhanced removal of toxic Congo red dye using multi walled
1744 carbon nanotubes: Kinetic, equilibrium studies and its comparison with other
1745 adsorbents. Journal of Molecular Liquids 212, 266-271.
1746 Zhang, J., Zou, H., Qing, Q., Yang, Y., Li, Q., Liu, Z., Guo, X., Du, Z., 2003. Effect of
1747 chemical oxidation on the structure of single-walled carbon nanotubes. The Journal of
1748 Physical Chemistry B 107, 3712-3718.
1749 Zhang, L., Petersen, E.J., Zhang, W., Chen, Y., Cabrera, M., Huang, Q., 2012. Interactions of
1750 ^{14}C-labeled multi-walled carbon nanotubes with soil minerals in water. Environmental
1751 Pollution 166, 75-81.
1752 Zhang, S., Shao, T., Bekaroglu, S.S.K., Karanfil, T., 2009. The impacts of aggregation and
1753 surface chemistry of carbon nanotubes on the adsorption of synthetic organic
1754 compounds. Environmental Science and Technology 43, 5719-5725.
1755 Zhao, H., Qiu, S., Wu, L., Zhang, L., Chen, H., Gao, C., 2014. Improving the performance of
1756 polyamide reverse osmosis membrane by incorporation of modified multi-walled
1757 carbon nanotubes. Journal of Membrane Science 450, 249-256.
1758 Zhao, M.-Q., Huang, J.-Q., Zhang, Q., Luo, W.-L., Wei, F., 2011. Improvement of oil
1759 adsorption performance by a sponge-like natural vermiculite-carbon nanotube hybrid.
1760 Applied Clay Science 53, 1-7.

Zhao, X., Jia, Q., Song, N., Zhou, W., Li, Y., 2010. Adsorption of Pb(II) from an aqueous solution by titanium dioxide/carbon nanotube nanocomposites: Kinetics, thermodynamics, and isotherms. Journal of Chemical and Engineering Data 55, 4428-4433.

Zou, Y., Wang, X., Khan, A., Wang, P., Liu, Y., Alsaedi, A., Hayat, T., Wang, X., 2016. Environmental remediation and application of nanoscale zero-valent iron and its composites for the removal of heavy metal ions: A review. Environmental Science and Technology 50, 7290-7304.